

Josephath Jeyabal Maria Praveena^{1*}, Jeyaraj Angelin Clara¹,
Susai Santhammal Rajendran¹, Antony John Amalraj²

¹PG and Research Department of Chemistry, Corrosion Research Centre St. Antony's College of Arts and Sciences for Women Thamarapady, Tamil Nadu, India, ²PG and Research Department of Chemistry, Periyar EVR Government College, Trichy, Tamil Nadu, India

Scientific paper

ISSN 0351-9465, E-ISSN 2466-2585

UDC: 665.7.038.5:669.141.24:535.361

<https://doi.org/10.5937/zasmat2104277P>



Zastita Materijala 62 (4)
277 - 290 (2021)

Inhibition of corrosion of mild steel in well water by an aqueous extract of soapnut (*Sapindus Trifoliatus*)

ABSTRACT

Inhibition efficiency of an aqueous extract of soapnut (*Sapindus Trifoliatus*) and Zn^{2+} in controlling corrosion of mild steel in well water at room temperature has been evaluated by using weight loss method, polarization study and AC impedance spectra. Dynamic light scattering and Vickers hardness have also been employed. Weight loss method reveals that the formulation consisting of 10 ml soapnut extract and 50 ppm Zn^{2+} has 97 % inhibition efficiency in controlling corrosion of mild steel immersed in well water. Synergism parameters suggest that a synergistic effect exists between soapnut extract and Zn^{2+} . Adsorption isotherm of metal surface obeys Langmuir adsorption isotherm. Polarization study reveals that the inhibitor system functions as anodic type of inhibitor. AC impedance spectra confirm the protective film formed on the metal surface. Dynamic light scattering (DLS) study reveals surface is in nano meter scale. The Vickers hardness of metal surface was increases in inhibitor system.

Keywords: *Sapindus Trifoliatus*, corrosion inhibitor, mild steel, well water, dynamic light scattering, Vickers hardness.

1. INTRODUCTION

Mild steel (also known as plain carbon steel) is a widely used material in the fabrication of heating and cooling water system in many industries [1-3]. Corrosion is nothing but the deterioration of material on exposure to corrosive environments like moisture or other chemicals. Ultimately it leads to the failure of that material. Corrosion is a problem that can never be avoided but can be controlled to a greater extent. Due to this destructive phenomenon, there have been various accidents reported. Therefore, preventing corrosion has been a very important economical need [4-6]. Researchers have focused primarily on plant-derived corrosion inhibitors due to their low cost and eco-friendly properties. The plant extracts such as *Ervatamia divaricate* [7], *Chrysanthemum Indicum* flower [8], *Commelina benghalensis* leaves

[9], *Acanthus montanus* leaves [10], *Lawsonia Inermis* L [11], *Diospyros kaki* (Persimmon) leaves [12], *Mentha pulegium* [13], *Ambrosia maritima* [14], *Solanum Xanthocarpum* Leaves [15] have been used as corrosion inhibitors.

The present research is focused on the effect of the aqueous extract of *Sapindustrifoliatus* as a corrosion inhibitor for mild steel corrosion in well water. Soapnut (*Sapindustrifoliatus*) (Figure 1) belongs to the family Sapindaceae. The plant is widely used in cosmetic preparation like shampoos and cleansers. Saponins are used for their effects on ammonia emissions in animal feeding [16,17]. Main active ingredient components of soapnut (*Sapindus trifoliatus*) is saponin (78.1%) (Figure 2).

The present study is undertaken:

- To evaluate the corrosion resistance of mild steel in well water, in presence of an green corrosion inhibitor soapnut extract (*sapindus trifoliatus*).
- To determine inhibition efficiency, synergism parameter and Langmuir adsorption isotherm from data derived from weight loss method.

*Corresponding author: J. J. M. Praveena

E-mail: Praveenaregan@gmail.com

Paper received: 18. 07. 2021.

Paper corrected: 24. 08. 2021.

Paper accepted: 05. 09. 2021.

Paper is available on the website: www.idk.org.rs/journal

- To develop Eco-friendly inhibitor system using readily available extract of plant sand Zinc for corrosion inhibition of mild steel in well water.
- To study the nature of process of corrosion inhibition and determine the type of inhibition whether anodic or cathodic or mixed using potentiodynamic polarization and Impedance studies.
- To examine the particle size Particle/molecular size, Size distribution, Relaxations in complex fluids by DLS method.
- To examine the hardness of metal surface by Vickers Hardness measurement.



Figure 1. Appearance of soapnut
Slika 1. Izgled sapunskog oraha

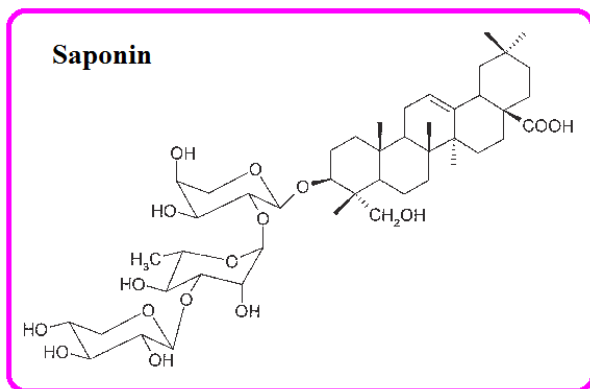


Figure 2. Structure of saponin
Slika 2. Struktura saponina

Saponins

Saponins are glucosides with foaming characteristics. Saponins consist of a polycyclic aglycones attached to one or more sugar side chains. The aglycone part, which is also called sapogenin, is either steroid (C27) or a triterpene (C30). The foaming ability of saponins is caused by the combination of a hydrophobic (fat-soluble) sapogenin and a hydrophilic (water-soluble) sugar

part. Saponins have a bitter taste. Some saponins are toxic and are known as sapotoxin. Soapnut contains 78.1% saponins.

2. MATERIALS AND METHODS

Preparation of inhibitor

10 g of soapnut fruit pulp was shade dried, weighed and boiled with double distilled water. The extract was filtered to remove suspended impurities and made up to 100ml. The soapnut (SN) extract used as corrosion inhibitor in the present study.

Preparation of mild steel (MS)

Mild steel (iron containing a small percentage of carbon, strong and tough but not readily tempered), also known as plain-carbon steel and low-carbon steel, is now the most common form of steel acceptable for many applications. Mild steel is malleable and ductile. Mild steel has a relatively low tensile strength, but it is cheap and easy to form; surface hardness can be increased through carburizing. Composition of mild steel is given in Table1. This mild steel has been used in making hull plates.

Mild steel specimens of dimension 1cm x 4 cm x0.2 cm were used in weight loss method. In electrochemical studies, the exposed area of mild steel was 1cm². The mild steel specimens were cleaned with different grade emery papers and degreased with acetone.

Well water

The physico-chemical parameters of well water are given in Table 2.

Table 2. Physico-chemical parameters of well water

Tabela 2. Fizičko-hemijski parametri bunarske vode

Parameters	Value
pH	8.38
Conductivity	1770µΩ ⁻¹ cm ⁻¹
Chloride	665ppm
Sulphate	214ppm
TDS	1100ppm
Total hardness	402ppm
Total Alkalinity	390ppm
Magnesium	83ppm
Potassium	55ppm
Sodium	172ppm
Calcium	88ppm

Table 1. Composition of MS

Tabela 1. Sastav MS

Name	unit	Average	Abs.Std.Dev	Ref.Std.Dev	1	2
C	%	0.101	0.0014	1.4	0.102	0.1
Si	%	0.055	0.0021	3.89	0.053	0.056
Mn	%	1.629	0.0057	0.35	1.633	1.625
P	%	0.0087	0.0003	3.25	0.0085	0.0089
S	%	0.0028	0.0003	10.1	0.0026	0.003
Cr	%	0.036	0.0014	3.93	0.037	0.035
Mo	%	0.0086	0.00007	0.83	0.0086	0.0085
Ni	%	0.033	0.0007	2.18	0.033	0.32
Cu	%	0.0063	0.00007	1.13	0.0062	0.0063
Al	%	0.044	0.0014	3.21	0.043	0.045
As	%	0.0011	0	0	0.0011	0.011
B	%	0.0027	0.0005	18.68	<0.00010	<0.00010
Bi	%	<0.00010	0.00002	84.85	<0.0025	0.003
Ce	%	0.0032	0.0013	42.65	0.0041	0.0022
Co	%	0.011	0	0	0.011	0.011
Mg	%	0.0003	0	0	0.0003	0.0003
Nb	%	0.03	0.0007	2.4	0.029	0.03
Pb	%	0.0081	0.0013	15.71	0.0072	0.009
Sb	%	0.004	0.0004	8.95	0.0037	0.0042
Sn	%	0.0034	0	0	0.0034	0.0034
Ta	%	0.03	0.0071	23.57	0.025	0.035
La	%	0.0071	0	0	0.0071	0.0071
Ti	%	0.0035	0	0	0.0035	0.0035
V	%	0.138	0.0014	1.02	0.137	0.139
W	%	0.071	0.0078	11.03	0.076	0.065
Zn	%	0.0024	0	0	0.0024	0.0024
Zr	%	0.0051	0.0002	0.2	0.0052	0.0049
Se	%	<0.0005	0.0001	4.42	<0.0005	<0.0005
N	%	0.0093	0.00007	0.76	0.0092	0.0093
Ca	%	0.0014	0.0001	10.1	0.0013	0.0015
Te	%	0.0026	0.0025	97.91	<0.0010	0.0044
Fe	%	97.74	0	0	97.74	97.74

Preparation of Zn²⁺ solution

1g of ZnSO₄·7H₂O salt was dissolved in distilled water and made up to 250 ml. 5 ml of this solution diluted to 100 ml gives 50 ppm of Zn²⁺.

Weight loss method

Weights of the three polished mild steel specimens were measured before and after immersion in various test solutions (100 ml). The inhibition efficiencies were calculated from the relation.

$$IE = [(CR_1 - CR_2) / CR_1] \times 100\% \quad (1)$$

where,

CR₁ is corrosion rate in the absence of inhibitor, and CR₂ is the corrosion rate in the presence of

inhibitor.

The immersion period was one day. The experiments were carried out at room temperature. Corrosion rate was calculated in mdd units:

Corrosion rate (mdd) = (weight loss in mg x surface area in dm²) / immersion period in days

Synergism parameters

To evaluate the synergistic effect existing between Zn²⁺ and soapnut extract, synergism parameters (S_i) were calculated. If S_i is parameter (S_i) greater than 1, it indicates the presence of synergistic effect, existing between Zn²⁺ and soapnut extract. To confirm this Synergism parameters (S_i) are calculated as shown, using the relation:

$$S_i = (1 - \theta_{1+2}) / (1 - \theta'_{1+2}) \quad (2)$$

where

$$\theta_{1+2} = (\theta_1 + \theta_2) - (\theta_1 \times \theta_2) \quad (3)$$

θ_1 = surface coverage by inhibitor 1 (soapnut extract)

θ_2 = surface coverage by inhibitor 2 (Zn^{2+})

θ'_{1+2} = Combined surface coverage by inhibitors 1 and 2.

Langmuir adsorption isotherm

There are various types of adsorption isotherms such as Langmuir, Freundlich and Temkin. In the case of Langmuir adsorption isotherm a plot of C vs C/ θ gives a straight line. Where C is concentration of the inhibitor and θ is surface coverage

$$\theta = \%IE/100 \quad (4)$$

Electrochemical study

In the present work corrosion resistance of mild steel immersed in various test solutions were measured by Polarization study and AC impedance spectra.

Polarization study

Polarization studies were carried out in a CHI Electrochemical work station analyzer, model 660A. It was provided with automatic iR compensation facility. A three electrode cell assembly was used (Figure 3). A SCE was the reference electrode.

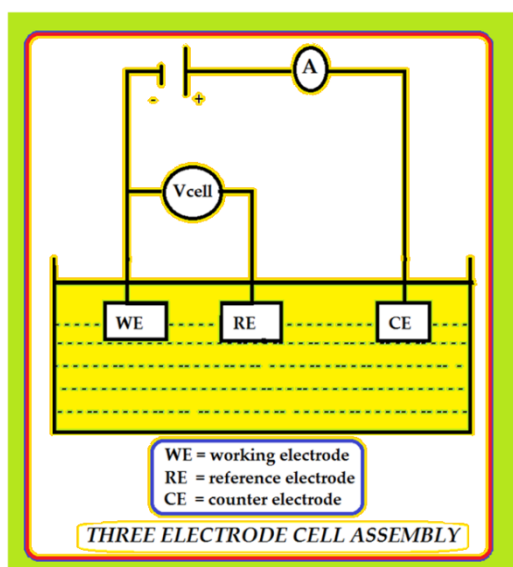


Figure 3. Three electrode cell assembly

Slika 3. Sklop ćelije sa tri elektrode

Platinum was the counter electrode. Mild steel was the working electrode. A time interval of 5 to

10 minutes was given for the system to attain a steady state open circuit potential. After having done IR compensation, polarization study was carried out at a sweep rate of 0.01 V/s. From polarization study, corrosion parameters such as corrosion potential (E_{corr}), corrosion current (I_{corr}), Tafel slopes anodic = b_{av} and cathodic = b_c and LPR (linear polarisation resistance) values were measured.

AC impedance spectra

The same instrument and set-up used for polarization study were used to record AC impedance spectra also. The real part (Z') and imaginary part ($-Z''$) of the cell impedance were measured in Ohms at various frequencies. AC impedance spectra were recorded with initial $E(V)=0$, high frequency ($Hz=1 \times 10^5$), low frequency ($Hz=1$), amplitude (V) = 0.005 and quiet time (s) = 2. From Nyquist plot the values of charge transfer resistance (R_t) and the double layer capacitance (C_{dl}) were calculated.

Dynamic light scattering (DLS)

Dynamic light scattering refers to measurement and interpretation of light scattering data on a microsecond time scale. Dynamic light scattering can be used to determine

- Particle/molecular size
- Size distribution
- Relaxations in complex fluids
- The experiments were carried out with particle size analyzer. Make : Micromeritics : Model : Nano plus

Vickers hardness

The carbon steel specimens immersed in various test solutions for one day were taken out, rinsed with double distilled water, dried and subjected to Vickers hardness measurement. The Vickers hardness measurements of the carbon steel surface were carried out by Shimadzu make model HMV-27.

3. RESULTS AND DISCUSSION

Weight loss method

Corrosion resistance of MS in well water, in presence of an inhibitor namely Soapnut extract in absence and presence of Zn^{2+} has been evaluated by weight loss method. The results are given in Table 3 and 4. It is observed from the Table 3 that soapnut extract has some inhibition efficiency (IE). As the concentration of soapnut extract increases, surface coverage (θ) increases, corrosion rate (CR, mdd) decreases and inhibition efficiency (IE,%) increases.

Table 3. Inhibition of corrosion of mild steel immersed in well water (without Zinc)

Tabela 3. Inhibicija korozije mekog čelika uronjenog u bunarsku vodu (bez cinka)

Soapnut extract (ml)	Zn ²⁺ (ppm)	Corrosion rate (mdd)	Inhibition efficiency (%)	Surface coverage (θ)
0	0	14.86	-	-
2	0	9.2132	38	0.38
4	0	8.7674	41	0.41
6	0	8.3216	44	0.44
8	0	7.8758	47	0.47
10	0	7.43	50	0.50

Influence of addition of Zn²⁺ on the inhibition efficiency (IE, %) of soapnut extract

Influence of addition of Zn²⁺ on the inhibition efficiency (IE, %) of soapnut extract is given in Table 4. It is observed that in presence of 50 ppm of Zn²⁺, the inhibition efficiency (IE, %) of soapnut extract increases tremendously. A synergistic effect exists between soapnut extract and Zn²⁺. A mixture of inhibitors shows better inhibition efficiency (IE, %) than that of individual members.

Synergistic effect

A mixture of inhibitors shows better inhibition efficiency (IE, %) than that of individual members. For example, 50 ppm of Zn²⁺ has 14% inhibition efficiency. 10 ml of soapnut extract has 50% inhibition efficiency. But their combination has 97% inhibition efficiency.

Table 4. Inhibition of corrosion of mild steel immersed in well water (with Zinc)

Tabela 4. Inhibicija korozije mekog čelika uronjenog u bunarsku vodu (sa cinkom)

Soapnut extract (ml)	Zn ²⁺ (ppm)	Corrosion rate (mdd)	Inhibition efficiency (%)	Surface coverage (θ)
0	0	14.86	-	-
2	50	2.229	85	0.85
4	50	1.7832	88	0.88
6	50	1.3374	91	0.91
8	50	0.8916	94	0.94
10	50	0.4458	97	0.97
0	50	12.7796	14	0.14

This confirms the synergistic effect existing between soapnut extract and Zn²⁺ (Table 5).

Table 5. Synergistic effect existing between soapnut extract and Zn²⁺

Tabela 5. Sinergijski efekat koji postoji između ekstrakta sapuna i Zn²⁺

System	Inhibition efficiency, %
50 ppm of Zn ²⁺	14
10 ml of soapnut extract	50
50 ppm of Zn ²⁺ and 10 ml of soapnut extract	97

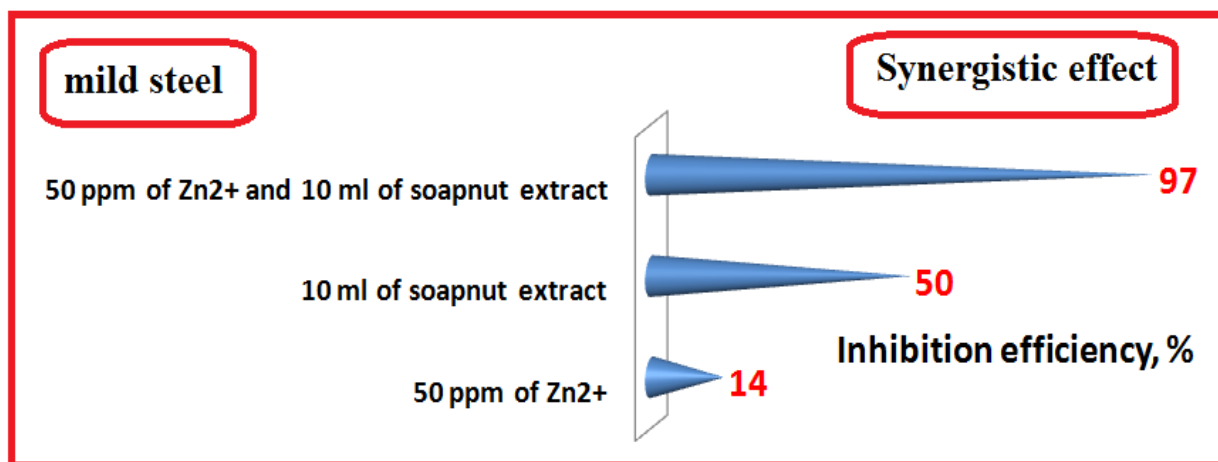


Figure 3. Synergistic effect

Slika 3. Sinergijski efekat

Synergism parameters

When two substances are used as corrosion inhibitors, synergistic effect is noticed between them. That is, a mixture of inhibitors shows better inhibition efficiency (IE, %) than that of individual members [18-21]. Synergism parameters (S_1) are calculated. If there is synergistic effect, the Synergism parameter (S_1) will be greater than 1. The Synergism parameters (S_1) calculated for various combinations of 10 ml of soapnut extract and (50 ppm of Zn^{2+}) are given in Table 6.

Table 6. Synergism parameters

Tabela 6. Parametri sinergizma

Soapnut extract, ml	θ_1	θ'_{1+2}	θ_2	θ_{1+2}	S_1
2	0.38	0.85	0.14	0.4668	3.56
4	0.41	0.88	0.14	0.4926	4.29
6	0.44	0.91	0.14	0.5184	5.35
8	0.47	0.94	0.14	0.5442	7.60
10	0.50	0.97	0.14	0.57	14.33

Langmuir adsorption isotherm

Soapnut extract system

The plot of C vs C/θ gives a straight line with R^2 value of 0.993 (Figure 4). Thus it is inferred that the adsorption soapnut extract on the metal surface obeys Langmuir adsorption isotherm.

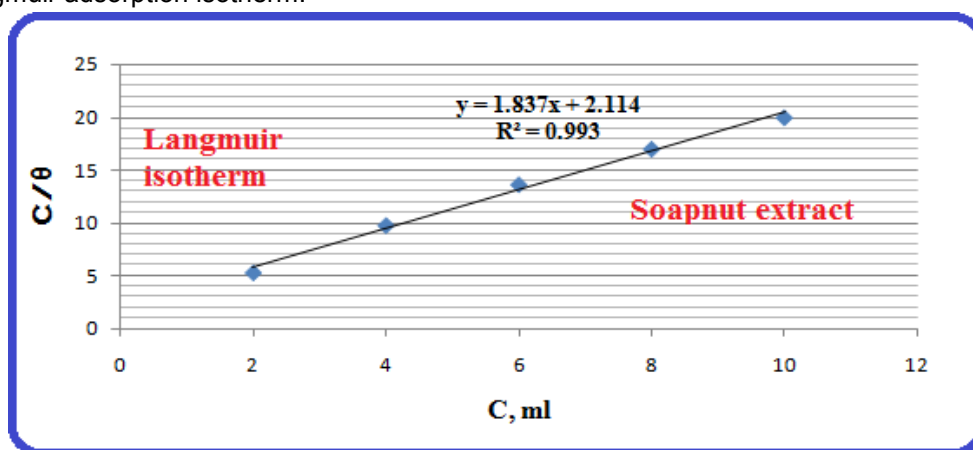


Figure 4. Langmuir adsorption isotherm for soapnut extract
Slika 4. Langmirova izoterma adsorpcije za ekstrakt sapuna

Soapnut extract - Zn^{2+} system

The plot of C vs C/θ gives a straight line with R^2 value of 0.998 (Figure 5). Thus it is inferred that the adsorption soapnut extract, in presence of Zn^{2+} , on the metal surface obeys Langmuir adsorption isotherm.

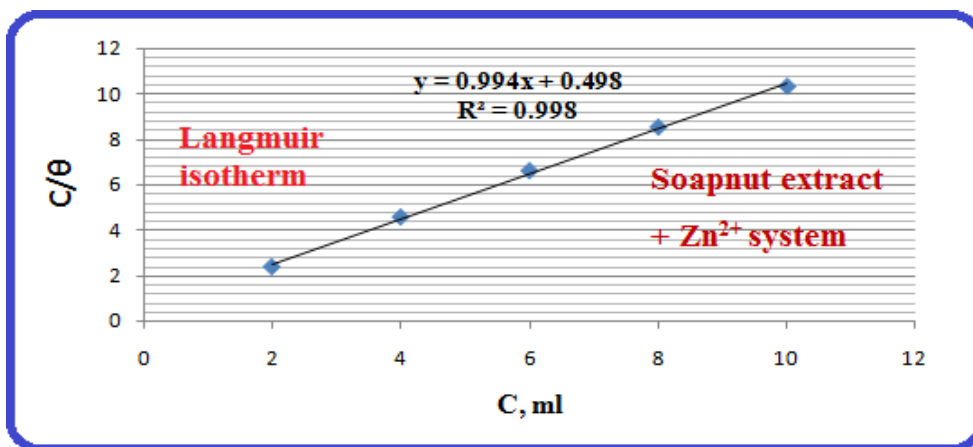


Figure 5. Langmuir adsorption isotherm for soapnut extract - Zn^{2+} system
Slika 5. Langmirova izoterma adsorpcije za ekstrakt sapun – Zn^{2+} sistem

Analysis of polarization study

Corrosion parameters derived from polarization study, namely corrosion potential (E_{corr}), Tafel slope (b_c , b_a), Linear Polarisation Resistance (LPR) values and Corrosion Current (I_{corr}) values are given in Table 7. The polarisation curves of mild steel immersed in well water in the absence and presence of inhibitor system are shown in Figure 6.

It is observed from the Table 7 that when mild steel is immersed in well water, the corrosion potential is -751 mV vs SCE, the LPR value is 711 Ohmcm². The corrosion current value is $6.082 \times 10^{-5} \text{ A/cm}^2$. It is inferred from the Table7, that in presence of inhibitor, the corrosion potential is shifted from -751mV to -549mV vs SCE. This indicates that a film is formed on the anodic sites of the metal surface. It suggests that the inhibitor system (soapnut extract - Zn²⁺) functions as anodic type inhibitor system [22,23]. The LPR value increases from 711 Ohmcm² to 1427 Ohmcm². Correspondingly the corrosion current value decreases from $6.082 \times 10^{-5} \text{ A/cm}^2$ to $3.066 \times 10^{-5} \text{ A/cm}^2$. These observations confirm that a

protective film is formed on the metal surface. This controls the corrosion of metal. If a protective film is formed on the metal surface, LPR value increases and corrosion current decreases.

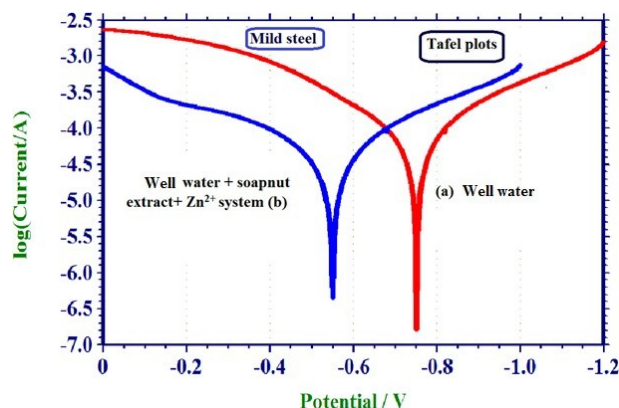


Figure 6. Polarization curves of mild steel immersed in various test solutions (a) well water, (b) well water + soapnut extract + Zn²⁺ system

Slika 6. Polarizacione krive mekog čelika uronjenog u različite test rastvore (a) bunarsku vodu, (b) bunarsku vodu + ekstrakt sapuna + Zn²⁺ sistem

Table 7. Corrosion parameters of mild steel immersed in well water in the absence and presence of inhibitor system [soapnut extract - Zn²⁺] obtained by polarization study

Tabela 7. Parametri korozije mekog čelika uronjenog u bunarsku vodu u odsustvu i prisustvu inhibitorskog sistema [ekstrakt sapuna - Zn²⁺] dobijeni ispitivanjem polarizacije

System	E_{corr} mV vs SCE	b_c mV/decade	b_a mV/decade	LPR Ohmcm ²	I_{corr} A/cm ²
Well water	-751	195	169	711	6.082×10^{-5}
Well water + soapnut extract (10 ml) + Zn ²⁺ (50 ppm)	-549	190	214	1427	3.066×10^{-5}

Analysis of AC impedance spectra

The protective film formed on the metal surface is confirmed by AC impedance spectra. If a protective film is formed on the metal surface, the charge transfer resistance (R_t) value increases; double layer capacitance value (C_{dl}) decreases and the impedance [$\log(Z/\text{ohm})$] value increases.

The AC impedance spectra of mild steel immersed in well water in the absence and presence of inhibitor [soapnut (sapindus trifoliatius) extract - Zn²⁺] are shown in Figure7. (Nyquist plots), Figures 8a and 8b (Bode plots). The corrosion parameters, namely R_t , C_{dl} , phase angle and impedance values are given in Table 8. It is observed from the Table 8 that, when mild steel is immersed in well water, the R_t value is 129.81 Ohmcm².

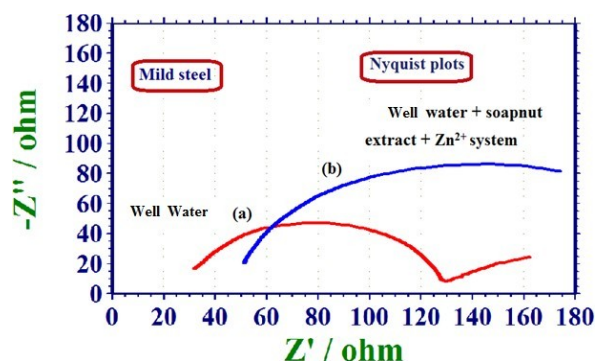


Figure 7. AC impedance spectra of mild steel immersed in various test solutions (a) well water, (b) well water + soapnut extract + Zn²⁺ system

Slika 7. Spektri impedanse naizmenične struje mekog čelika uronjenog u različite test rastvore (a) bunarsku vodu, (b) bunarsku vodu + ekstrakt sapuna + Zn²⁺ sistem

The C_{dl} value is 3.929×10^{-8} F/cm². The impedance value is 2.213. The phase angle value is 37.35. In the presence of inhibitor system, the R_t value increases from 129.81 Ohmcm² to 398.57

Ohmcm². The C_{dl} value decreases from 3.929×10^{-8} F/cm² to 1.2795×10^{-9} F/cm². The impedance value increases from 4.084 to 4.153. The phase angle value increases from 37.35 to 39.12 [24,25].

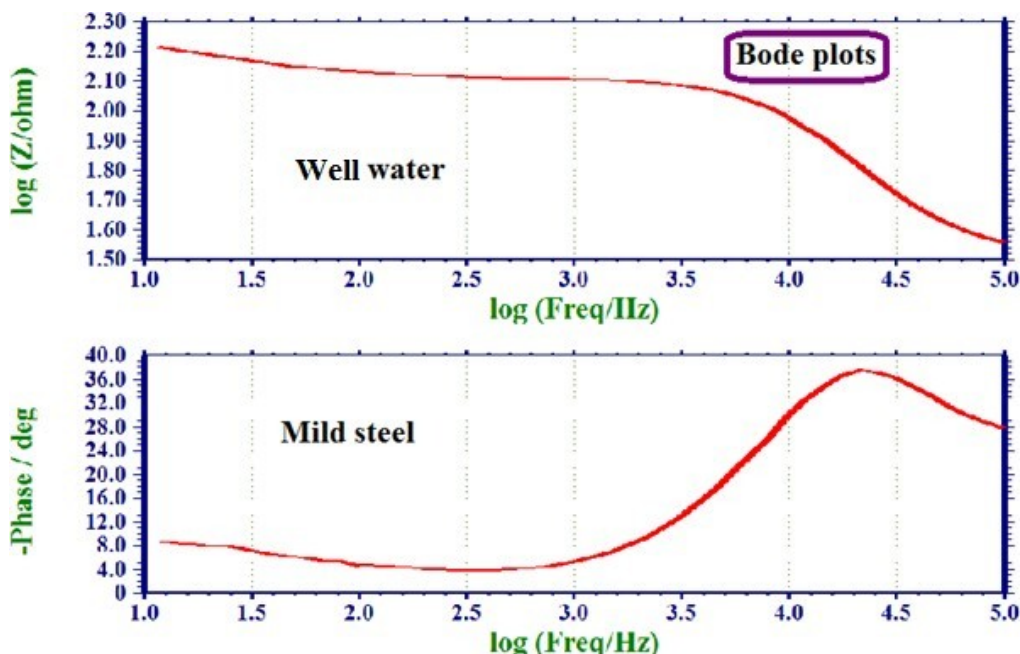


Figure 8a. AC impedance spectra of mild steel immersed in well water (Bode plots)

Slika 8a. Spektri impedanse naizmenične struje mekog čelika uronjenog u bunarsku vodu (Bode grafike)

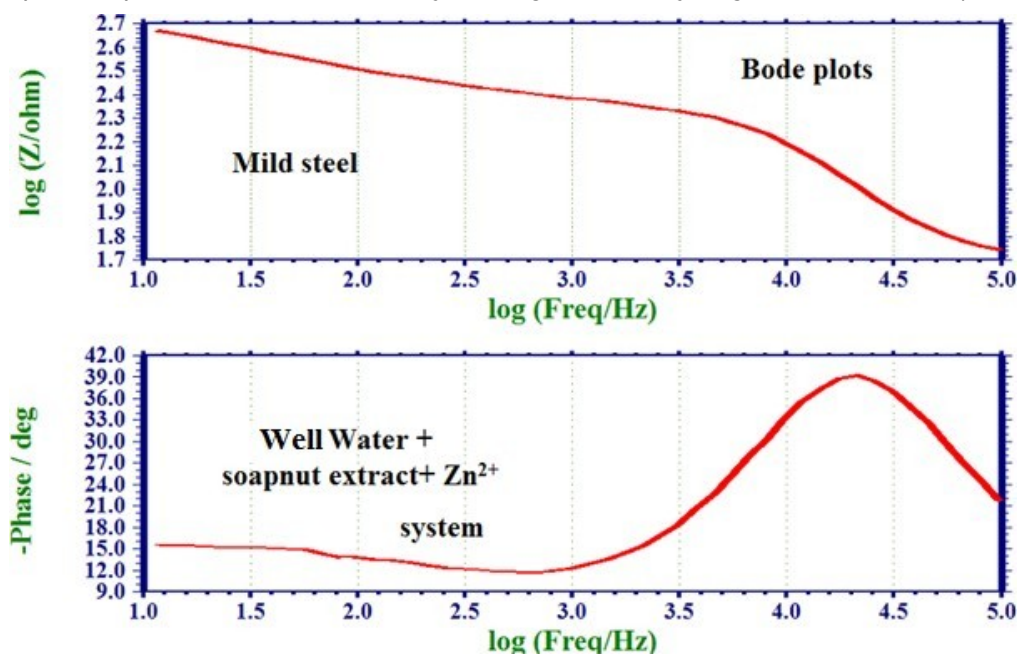


Figure 8b. AC impedance spectra of mild steel immersed in well water + soapnut extract + Zn²⁺ system (Bode plots)

Slika 8b. Spektri impedanse naizmenične struje mekog čelika uronjenog u bunarsku vodu + ekstrakt sapuna + Zn²⁺ sistem (Bode grafikoni)

Table 8. Corrosion parameters of mild steel immersed in well water in the absence and presence of inhibitor system (Soapnut extract - Zn²⁺) obtained by AC impedance spectra

Tabela 8. Parametri korozije mekog čelika uronjenog u bunarsku vodu u odsustvu i prisustvu inhibitornog sistema (ekstrakt soapnut - Zn²⁺) dobijeni spektrom impedanse naizmenične struje

System	R _t Ohmcm ²	C _{dl} F/cm ²	Impedance log(Z/Ohm)	Phase angle (°)
Well water	129.81	3.929×10 ⁻⁸	2.213	37.35
Well water + soapnut extract (10 ml) + Zn ²⁺ (50 ppm)	398.57	1.2795×10 ⁻⁸	2.667	39.12

Equivalent circuit diagrams

The Nyquist plot of the blank system is characteristic of a film forming and film breaking system. The inhibited system has one time constant. The equivalent circuit diagrams shown in Figures 9 and 10.

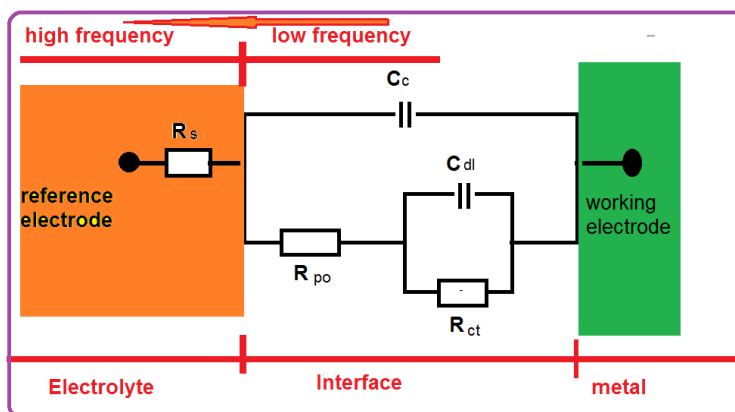


Figure 9. Equivalent circuit diagram for blank system (film formation and film breaking)

Slika 9. Ekvivalentna šema za blank sistem (formiranje filma i lomljenje filma)

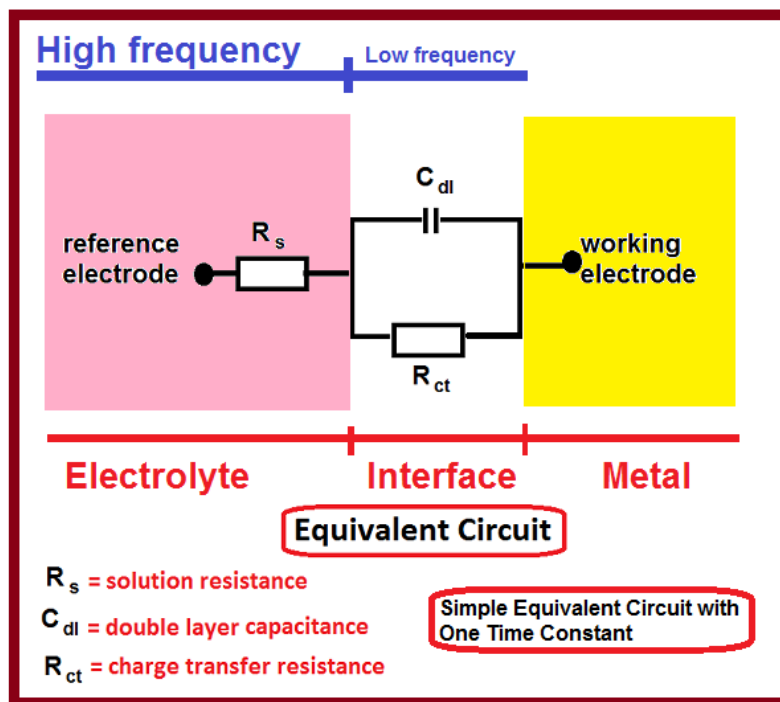


Figure 10. Equivalent circuit diagram for inhibited system (one time constant)

Slika 10. Ekvivalentna šema kola za blokirani sistem (jedna vremenska konstanta)

Dynamic light scattering

The particle size of protective film ranges from 30-990 nm. The size of the protective and the polydispersity index have been calculated by dynamic light scattering method. The results are shown in Figures 11 and 12 and Table 9, 10, 11.

The average diameter of protective film is 148.7 nm. This is the width in the nanometer scale. The polydispersity index is 0.240. This indicates homogeneous nature of the protective film. The diffusion constant is 3.308×10^{-8} (cm²/sec). The intensity distribution curve is shown in Figure 11. ACF of soapnut extract-Zn²⁺ system is shown in Figure 12.

Table 9. Distribution Results

Tabela 9. Rezultati

Peak	Diameter (nm)	Std. Dev
1	234.8	183.9
2	0.0	0.0
3	0.0	0.0
4	0.0	0.0
5	0.0	0.0
Average	234.8	183.9
Residual	1.958e-003	(O.K)

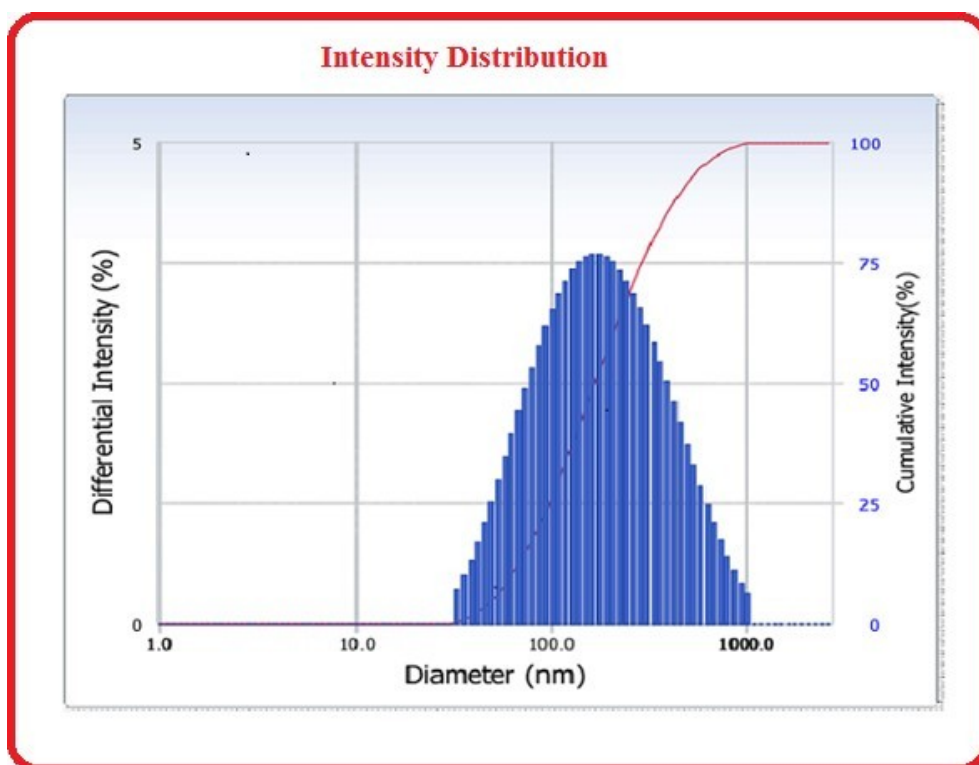


Figure 11. Intensity distribution curve
Slika 11. Kriva raspodele intenziteta

Table 10. Cumulants Results

Tabela 10. Kumulativni rezultati

Diameter (d)	148.7 (nm)
Polydispersity Index (P.I.)	0.240
Diffusion constant (D)	3.308×10^{-8} (cm ² /sec)

Table 11. Measurement condition

Tabela 11. Uslovi merenja

Diluent name	Water
Refractive Index	1.3328
Temperature	25°C
Viscosity	0.8878 (cP)
Scattering Intensity	31311 (cps)
Attenuator 1	12.61 %

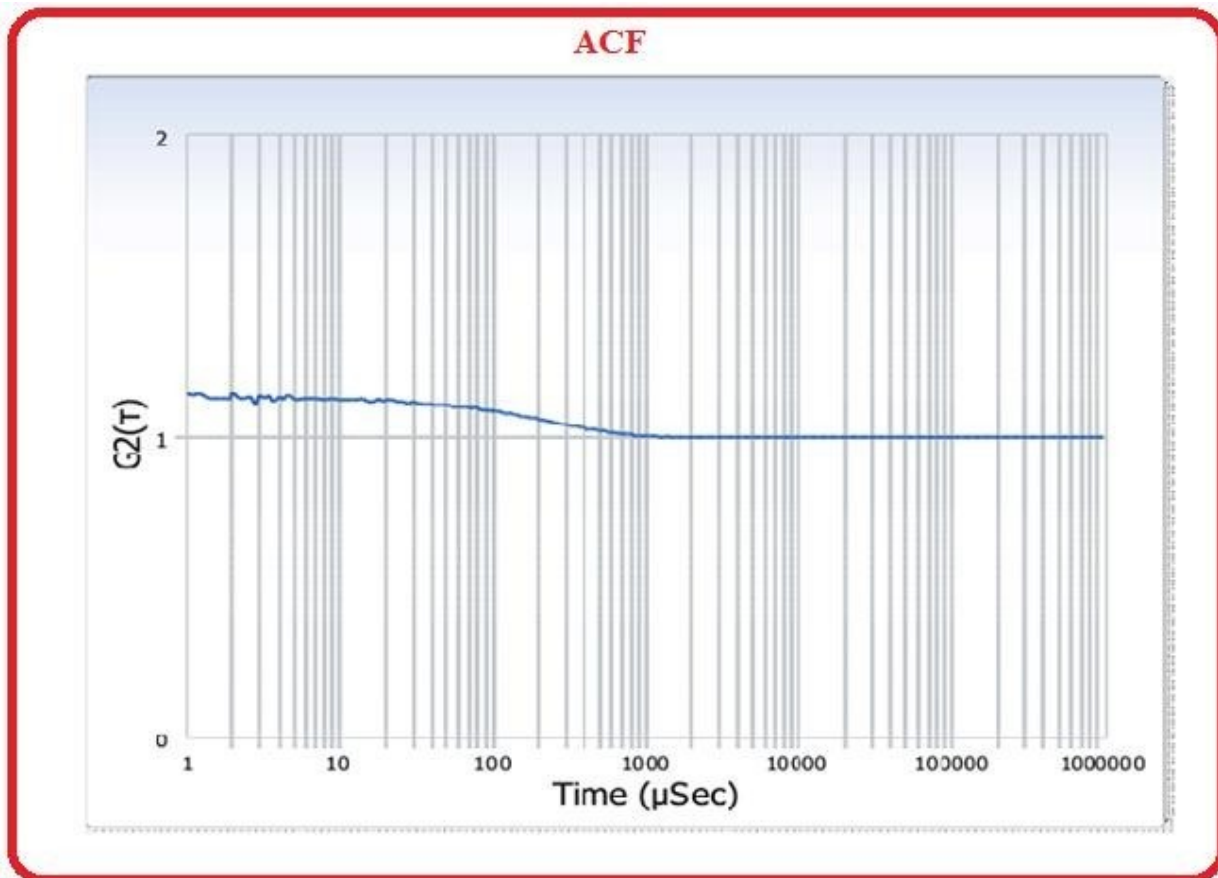


Figure 12. ACF of soapnut extract-Zn²⁺ system
 Slika 12. ACF ekstrakta sapun - Zn²⁺ sistem

Analysis of Vickers hardness

The Vickers test is often easier to use than other hardness tests since the required calculations are independent of the size of the indenter, and the indenter can be used for all materials irrespective of hardness. The basic principle, as with all common measures of hardness, is to observe a material's ability to resist plastic deformation from a standard source. The Vickers test can be used for all metals and has one of the widest scales among hardness tests. The unit of hardness given by the test is known as the Vickers Pyramid Number (HV).

The hardness was measured for polished mild steel surface (system A), polished mild steel surface immersed in corrosive medium (well water) (system B) and polished mild steel surface immersed in corrosive medium (well water) containing the inhibitor system (system C). The values are given in Table 12. It is observed that for system A the hardness is high. For system B the hardness is low, because the corroded surface contains iron oxide film which is porous and amorphous. The

surface is very rough. Pits are noticed due to corrosion. For system C the surface is smooth, due to the formation of protective film (Figure 13). Usually the hardness is in between that of system A and B. That is, lower than that of polished metal but higher than that of corroded surface. This is due to the formation of a protective film on the metal during corrosion inhibition process. The protective film consists of iron inhibitor (active principles) complex. Thus the Vickers hardness is used in corrosion inhibition study. Weight loss method reveals that addition of 10 ml of 10% soapnut extract offers an inhibition efficiency of 97 % to carbon steel immersed in well water.

Table 12. HV for 300 gram load

Tabela 12. HV za opterećenje od 300 grama

System	Load	L1	L2	HV
Polished metal	300 g	54.90	55.29	183
Corroded metal	300 g	70.27	72.59	109
Inhibited metal	300 g	60.29	61.66	150

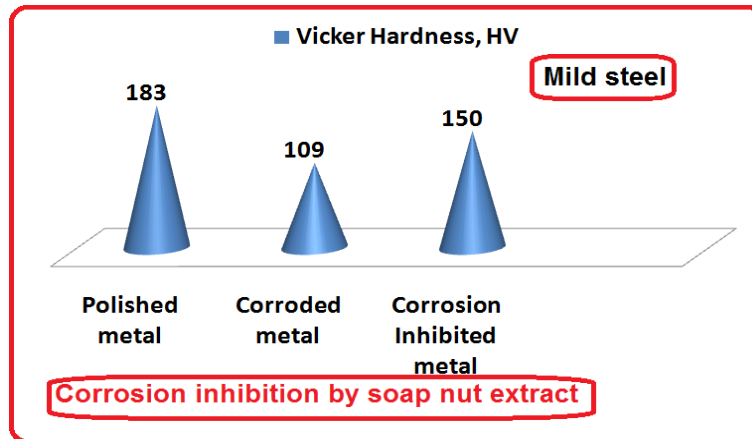


Figure 13. Hardness of various surfaces (300 g load)
 Slika 13. Tvrdoća raznih površina (opterećenje 300 g)

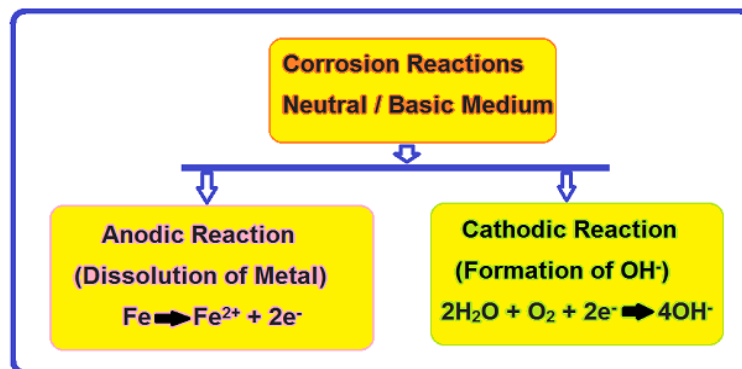


Figure 14. Anodic and cathodic reactions in corrosion process
 Slika 14. Anodne i katodne reakcije u procesu korozije

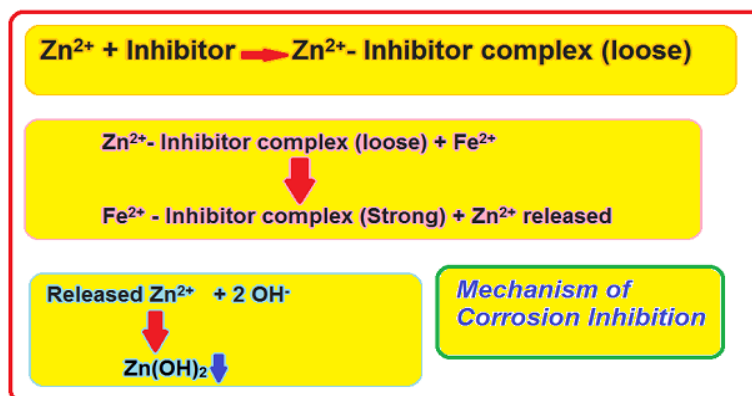


Figure 15. Mechanism of corrosion inhibition
 Slika 15. Mehanizam inhibicije korozije

Mechanism of corrosion inhibition

In presence of Zn²⁺, corrosion resistance of the metal further increases (better than the inhibitor system alone), which is supported by the fact that the linear polarisation resistance value further increases and corrosion current value further

decreases. Similarly during electrochemical impedance study, charge transfer value increases tremendously and double layer capacitance value decreases to a great extent. It is inferred that in presence of Zn²⁺, more inhibitor molecules (active ingredients of the plant extract) are transported

towards the metal surface, as Zn^{2+} – inhibitor complex. On the metal surface iron inhibitor complex is formed on the anodic sites of the metal surface and Zn^{2+} is released. The released Zn^{2+} combines with OH^- to form $Zn(OH)_2$ complex on the cathodic sites of the metal surface. Thus in presence of Zn^{2+} , both anodic reaction and cathodic reaction are controlled effectively. This accounts for the increase in corrosion resistance of metal well water in presence of inhibitor and Zn^{2+} . In presence of Zn^{2+} and inhibitor a loose complex is formed between Zn^{2+} and inhibitor. The bond between them is strong enough to carry the inhibitor to the metal surface and weak enough to release the inhibitor in presence of Fe^{2+} to form Fe^{2+} –inhibitor complex on the anodic sites of the metal surface (Figures 14 and 15).

CONCLUSIONS

Useful conclusions are derived from the interpretation of the experimental data.

- Weight loss method reveals that soapnut extract- Zn^{2+} system offers a maximum corrosion inhibition efficiency of 97% in controlling corrosion of mild steel in well water.
- Synergism parameters are found to be greater than 1, confirming the
- synergistic effect existing between soapnut extract and Zn^{2+} .
- Langmuir adsorption isotherm: Adsorption of inhibitor molecules
- on the metal surface obeys Langmuir adsorption isotherm.
- Polarisation Study reveals that the inhibitors namely aqueous extract of soapnut extract- Zn^{2+} system functions as anodic type of inhibitor.
- AC impedance spectra confirm the formation of a protective film on the metal surface.
- The DLS study reveals that the protective film formed on the surface is in nanometer scale.
- The hardness of metal surface increases in inhibitor system. It has been measured by Vickers Hardness.
- This formulation of soapnut extract- Zn^{2+} may be used in cooling water systems, where mild steel pipelines are used to carry well water which is used as coolant.

REFERENCES

- [1] T.Sathiyapriya, G.Rathika (2019) Corrosion inhibition efficiency of human black hair extract on mild steel in 1 M H_2SO_4 media, Indian Journal of Chemical Technology, 26, 216-223.
- [2] B.N.Grgur (2020) Corrosion of the stainless steel 316Ti in 10% hydrochloric and sulfuric acid, Zastita Materijala, 61(4), 339-346.
- [3] S.Rajendran, V.Sribharathy, A.Krishnaveni, J.Jeyasundari, J.Sathiyabama, T.S.Muthumegala, M.Manivannan (2011) Inhibition effect of self assembled films formed by adipic acid molecules on carbon steel surface, Zastita materijala, 52(3), 163-172.
- [4] S.Sheetal, A.Prakash, Y.Raj, M.Harilal, J.Felix Kumar (2020) A review on the Enhanced Corrosion Control of Mild Steel in an Acidic Medium using Green Inhibitors, International Research Journal of Engineering and Technology (IRJET), 7(6), 4085-4093.
- [5] A.El-Aziz S.Fouda, A.Y.El-Khateeb, N.M. Elbahrawi (2017) Cupressus sempervirens extract as green inhibitor for corrosion of carbon steel in hydrochloric acid solutions, Zastita Materijala, 60 (2), 129-146.
- [6] A.El-Aziz S. Fouda, A.H.Ali (2018) Egdronate drug as promising corrosion inhibitor of C - steel in aqueous medium, Zastita Materijala, 59 (1), 126-140.
- [7] P.Shanthi, J.A.Thangakani, S.Karthika, S.C.Joyce, S.Rajendran, J.Jeyasundari (2021) Corrosion inhibition by an aqueous extract of *Ervatamia divaricate*, International Journal of corrosion and Scale Inhibition, 10(1), 331-348.
- [8] H.Zhang, Z.Ni, H.Wu, P.Xu, Z.Li, W.Zhang, H. Huang, Q.Zhou, X.Yue, Ji.Bao, X.Li (2020) Corrosion Inhibition of Carbon Steel in Hydrochloric Acid by *Chrysanthemum Indicum* Extract, International Journal of Electrochemical Science, 15, 5487 - 5499.
- [9] K.Riaz Ahamed, B.Arifa Farzana, S.J.Diraviam, R. Dorothy, S.Rajendran, A.Al-Hashem (2019) Mild Steel Corrosion inhibition by the Aqueous Extract of *Commelina benghalensis* Leaves, Portugaliae Electrochimica Acta, 37(1), 51-70.
- [10] G.I.Udom, G.A.Cookey, A.A.Abia (2017) The Effect of *Acanthus montanus* Leaves Extract on Corrosion of Aluminium in Hydrochloric Acid Medium, Current Journal of Applied Science and Technology, 25(2), 1-11.
- [11] S.Rajendran, M.Agasta, R.B.Devi, B.S.Devi, K. Rajam, J.Jeyasundari (2009) Corrosion inhibition by an aqueous extract of Henna leaves (*Lawsonia Inermis L*), Zastita Materijala, 50, 77-84.
- [12] H.Gerengi, Il.Uygur, M.Solomon, M.Yildiz, H.Goksu (2016) Evaluation of the inhibitive effect of *Diospyros kaki* (Persimmon) leaves extract on St37 steel corrosion in acid medium, Sustainable Chemistry and Pharmacy, 4, 57-66.
- [13] Ab.Khadraoui, Ab.Khelifa, K.Hachama, H. Boutoumi, B.Hammouti (2015) Synergistic effect of potassium iodide in controlling the corrosion of steel in acid medium by *Mentha pulegium* extract, Res Chem Intermed, 41, 7973-7980.
- [14] H.M.Elabbasy, S.M.Zidan, Abd El-Aziz S. Fouda (2019) Inhibitive behavior of *ambrosia maritima* extract as an eco-friendly corrosion inhibitor for carbon steel in 1M HCl, Zastita Materijala, 59 (1), 126-140.

- [15] K.Hema, B.R.Venkatraman, A.Sirajunnisa, A. Subramania (2015) The Effect of Solanum Xanthocarpum Leaves Extract on Corrosion Inhibition of Carbon Steel in Acidic Medium, International Journal of Advanced Research in Chemical Science, 2(9), 10-20.
- [16] E.Zentner (2011) Effects of phytogenic feed additives containing quillaja saponaria on ammonia in fattening pigs (PDF), Retrieved 27 November 2012
- [17] M.Sangeetha, S.Rajendran, N.Pavazhanayagam, C.Sobiga, P.Valentine Nancy (2016) Corrosion resistance of SS 316 L alloy in artificial saliva in the presence of a soft drink, Der Pharma Chemica, 8, 334-337.
- [18] A.M.Ridhwan, A.A.Rahim, A.M.Shah (2012) Synergistic effect of halide ions on the corrosion inhibition of mild steel in hydrochloric acid using mangrove tannin. International Journal of Electrochemical science, 7, 8091-8104.
- [19] K.S.Shaju, K.Job Thomas, V.P.Raphael, A.Paul (2012) Synergistic effect of KI on corrosion inhibition of mild steel by polynuclear Schiff base in sulphuric acid, Corrosion, 1-8, Article ID 425878.
- [20] K.Aramaki, M.Hackerman (1969) Inhibition mechanism of medium sized polymethyleneimine, Journal of the electrochemical society, 116(5), 568-574.
- [21] V.R.Nazeera Banu, V.Ramesh Babu, S.Rajendran (2017) Investigating the corrosion inhibition efficiency of surgical carbon steel instruments used in medical field, International Research Journal of Pharmacy, 8(12), 79-90.
- [22] M.Lavanyaa, M.Suganya (2016) Comparative analysis of corrosion inhibition studies on various metals in oil well water using trisodium citrate as inhibitor, International Journal of Nano Corrosion Science and Engineering, 3(4), 88-103.
- [23] D.Lakshmi, J.Sathiyabama, S.Rajendran (2017) The inhibition effect of o-nitrophenol and Zn²⁺ system on corrosion of aluminium, International Journal of Corrosion and Scale Inhibition, 6(3), 240-261.
- [24] K.Anuradha, R.Vimala, B.Narayanasamy, J.Arockia Selvi, S.Rajendran (2008) Corrosion Inhibition of Carbon Steel in Low Chloride Media by an Aqueous Extract of Hibiscus rosa-sinensis Linn, Chem. Eng. Comm., 195, 352-366.
- [25] A.Suriya Prabha, K.Kavitha, H.Benita Sherine, S.Rajendran (2020) Inhibition of corrosion of mild steel in simulated oil well water by an aqueous extract of Andrographis paniculata, Indian Journal of chemical Technology, 27, 452-460.

IZVOD

INHIBICIJA KOROZIJE MEKOG ČELIKA U BUNARSKOJ VODI VODENIM EKSTRAKTOM SAPUNA (*SAPINDUS TRIFOLIATUS*)

Efikasnost inhibicije vodenog ekstrakta sapuna (Sapindus Trifoliatum) i Zn²⁺ u kontroli korozije mekog čelika u bunarskoj vodi na sobnoj temperaturi je procenjena primenom metode gubitka težine, studije polarizacije i spektra impedanse naizmjenične struje. Takođe, korišćeno je dinamičko rasejanje svetlosti i tvrdoća po Vickersu. Metoda gubitka težine otkriva da formulacija koja se sastoji od 10 ml ekstrakta sapuna i 50 ppm Zn²⁺ ima 97% efikasnost inhibicije u kontroli korozije mekog čelika uronjenog u vodu iz bunara. Parametri sinergizma sugerišu da postoji sinergistički efekat između ekstrakta sapuna i Zn²⁺. Izoterma adsorpcije metalne površine je podređena Langmuir adsorpcionoj izotermi. Studija polarizacije otkriva da inhibitorni sistem funkcioniše kao anodni tip inhibitora. Spektri impedanse naizmjenične struje potvrđuju zaštitni film formiran na površini metala. Studija dinamičkog rasejanja svetlosti (DLS) otkriva da je površina u nanometarskoj skali. Vickersova tvrdoća metalne površine je povećana u sistemu inhibitora.

Ključne reči: *Sapindus Trifoliatum*, inhibitor korozije, meki čelik, bunarska voda, dinamičko rasejanje svetlosti, tvrdoća po Vickersu.

Naučni rad

Rad primljen: 18. 07. 2021.

Rad korigovan: 24. 08. 2021.

Rad prihvaćen: 05. 09. 2021.

Rad je dostupan na sajtu: www.idk.org.rs/casopis