

Pavel Anatolyevich Nikolaychuk<sup>1,2\*</sup>

<sup>1</sup>Kurganskij gosudarstvennyj universitet, Kurgan, Russian Federation

<sup>2</sup>Novosibirskij gosudarstvennyj universitet, Novosibirsk, Russian Federation

Scientific paper

ISSN 0351-9465, E-ISSN 2466-2585

<https://doi.org/10.62638/ZasMat999>



Zastita Materijala 65 ( )  
(2024)

## Inhibitory properties of the boiling extracts from *Fagus sylvatica purpurea* fallen leaves on the corrosion of mild steel in acidic environments

### ABSTRACT

The inhibitory ability of boiling extracts from the fallen leaves of *Fagus sylvatica purpurea* on the corrosion of mild steel EN Fe37-3FN in 0.5 M hydrochloric acid and 0.5 M sulphuric acid media was investigated using gravimetric, electrochemical, and EIS methods. The results show that the addition of 100 mg/L of *Fagus sylvatica purpurea* fallen leaf extract reduces the corrosion rate by 20–25%, while the addition of 1 g/L or more reduces it by 65–70%. The adsorption of the extract components on the steel surface follows the Langmuir adsorption model, and the nature of the adsorption is physical. The *Fagus sylvatica purpurea* fallen leaf extract demonstrates potential as an environmentally friendly substance for reducing steel corrosion rates in acidic environments.

**Keywords:** *Fagus sylvatica purpurea*, purple beech, boiling extracts, acid medium corrosion inhibition, mild steel, gravimetric study, electrochemical study, electrochemical impedance spectroscopy, Langmuir adsorption isotherm.

### 1. INTRODUCTION

The usage of industrial side products and wastes [1], expired drugs [2], food and biomass waste [3, 4] and compounds extracted from natural products [4] attracts a growing interest of the corrosion engineers around the globe. By employing environmentally degradable natural compounds one could drastically reduce the costs and the ecological impact of both production of inhibitors, and their subsequent utilisation. A plant's roots, leaves, aerial parts, fruits, and seeds are frequently used as the source of extracted compounds [4].

The purple beech (*Fagus sylvatica purpurea*) is a cultivar of the European beech, which is widely distributed in several parts of Europe, Middle Asia and North America [5]. Due to its unusual purple colour of leaves, it is commonly used as the ornamental tree. The bark and the leaf of the European beech are well-known strong antioxidants [6, 7], and contain several polyphenolic compounds including

phenolic acids and flavonoids [7–9]. However, both flavonoids [10,11] and phenols [11] exhibit inhibitory properties on metal oxidation. Moreover, there is a clear dependency between the antioxidant and inhibition properties of natural compounds [12], and therefore, the compounds extracted from *Fagus sylvatica* leaves might be useful and environmentally friendly corrosion inhibitors.

Acidic environments are often employed for the study of the effectiveness of inhibitors, because acids give the most demonstrative results [11]. In addition, the study of the acidic corrosion of metals is important for oil and gas industry, the galvanic electroplating of metals, the development of the solutions for the metal pickling, and for the rust removal [11]. Only a single study concerning the usage of extract of the common beech leaves as the inhibitor of the corrosion of carbon steel in sulphuric acid was already published [13]. However, in that paper a commercial ethanolic extract was used, and its concentration was not specified, therefore, it is impossible to understand the dependency on the inhibitory properties on the concentration of the extracted compounds. Moreover, the employment of toxic organic extractant undermines the sustainability of the obtained extract. The usage of boiling water extract seems a more environmentally friendly solution.

Corresponding author: Pavel Anatolyevich Nikolaychuk

E-mail: [pavel.nikolaychuk@kgsu.ru](mailto:pavel.nikolaychuk@kgsu.ru)

Paper received: 29. 02. 2024.

Paper corrected: 24. 09. 2024.

Paper accepted: 01. 10. 2024.

At the end of September, the beech tree exhibits the leaf fall producing the considerable amount of fallen leaves. It was previously found [8] that the concentration of the bioactive compounds in the beech leaves remain stable till the leaf fall. Therefore, collecting the freshly fallen leaves and extracting phenolic compounds from them is a sustainable way to produce extract without jeopardising the growing tree.

Therefore, in the present study, the inhibitory properties of the boiling extracts of the *Fagus sylvatica purpurea* freshly fallen leaves on the corrosion of mild steel EN Fe37-3FN in 0.5 M hydrochloric acid and 0.5 M sulphuric acid media are aimed to be investigated.

## 2. METHODS

### 2.1. Reagents and Equipment

Ethanol (analytical grade) and hydrochloric and sulphuric acids (pure grade) were purchased from LLC "Sigma Tek". Steel electrodes were manufactured from cylindrical ingots made of mild steel EN Fe37-3FN (containing no more than 0.14% C, 0.3% Ni, Cu, and Cr, 0.05% Si, 0.4% Mn, 0.05% P and 0.04% S). The unused flat end surface of the ingots was sealed by the epoxy resin, and the cylindrical working surface immersed in the solution was equal to 0.04 cm<sup>2</sup>.

Weighting of the samples was performed using the analytical balance EX224/AD (Ohaus Corp.). Electrochemical and EIS measurements were conducted using the potentiostat-galvanostat PS-50 (LLC "SmartStat"). The mercury-mercurous sulphate reference electrode by Schott Instruments GmbH was used. A water for solution preparation was first distilled using the aquadistiller AE-15 (LLC "Livam") and then deionised using the water purification system AkvaLab S18 (LLC "Akvalab"). The magnetic stirrer MS-200 LT (LLC "Labtex") was used for stirring and heating the solutions. The single-channel laboratory pipettes manufactured by Thermo Fisher Scientific were used for pipetting the solutions. A laboratory glassware of 2nd grade was used.

### 2.2. Preparation of the Extracts

The freshly fallen leaves of the purple beeches (*Fagus sylvatica purpurea*) were collected in early October from the trees located in the woods in the outskirts of Novosibirsk, Russia. The leaves were air-dried in the absence of the direct sunlight during three months and subsequently ground.

A total of 100 g of dried and ground *Fagus sylvatica purpurea* leaves were weighted, immersed into a litre of the deionised water, heated and boiled under the reflux condenser during 3 h. The boiling extracts were cooled, the plant material

was removed, and the solid residues were filtered off through the filter paper with the pore diameter of 12 µm.

A total of 10 ml of the extract was taken, placed in a beaker and heated to dryness in order to determine the mass of the dissolved substances and the initial concentrations of the extract solutions. Then the working solutions of the *Fagus sylvatica purpurea* leaf extract with the concentrations ranging from 0.2 to 20 g/l were prepared by the appropriate dilutions. The solutions were then equally diluted by 1 M hydrochloric acid or by 1 M sulphuric acid to finally produce a series of acidic solutions of *Fagus sylvatica purpurea* leaf extract in 0.5 M HCl or 0.5 M H<sub>2</sub>SO<sub>4</sub> with concentrations ranging from 0.1 to 10 g/l.

### 2.3. Gravimetric studies

For gravimetric tests, rectangular flat plates made of EN Fe37-3FN mild steel with thickness 3 mm, width 20 ± 2 mm, and height 30 ± 2 mm were polished using the P2500 emery paper and degreased by ethanol. The weighted plates ( $m_0$ ) were immersed into corrosive media for 2 h, then washed with distilled water, dried, and reweighted ( $m$ ). Each experiment was performed in triplicate. From the measured weight losses ( $\Delta m = m_0 - m$ ), sample surfaces ( $S$ ), and immersion times ( $t$ ) the average corrosion rates ( $\omega$ ) were estimated [11]:

$$\omega = \Delta m / (S \cdot t). \quad (1)$$

An inhibitory ability (IE) of the compound was estimated from the ratio of the corrosion rates in the absence ( $\omega_0$ ) and in the presence ( $\omega$ ) of the inhibitor [11]:

$$IE = (\omega_0 - \omega) / \omega_0 \cdot 100\%. \quad (2)$$

### 2.4. Polarisation studies

For polarisation tests, electrodes made of EN Fe37-3FN mild steel and sealed with the epoxy resin with the working surface of 0.04 cm<sup>2</sup> were polished using the P2500 emery paper and degreased by ethanol. The measurements were conducted in a standard three-electrode electrochemical cell, consisting from the working electrode (steel sample), auxiliary electrode from the porous graphite, and the mercury-mercurous sulphate reference electrode. An open circuit potential ( $E_{corr}$ ) was recorded during 30 min.

For the measurement of the linear polarisation resistance the polarisation curves were recorded in the current range from -10 µA and to +10 µA in galvanodynamic mode with the current sweep rate of 2 µA/s. Each experiment was performed in triplicate. The obtained polarisation curves were presented in the coordinates  $E(I)$ , and the polarisation resistances were evaluated as the slopes of these curves using the least squares technique:

$$R_p = dE / dl. \tag{3}$$

The inhibitory ability of the compound was estimated from the ratio of the polarisation resistances in the presence ( $R$ ) and in the absence ( $R_0$ ) of the inhibitor [11]:

$$IE = (R - R_0) / R \cdot 100\%. \tag{4}$$

For the measurement of the Tafel slopes [14] and the corrosion current density the polarisation curves were recorded in both directions in the potential ranges from the measured open circuit potential to  $-500$  mV and to  $+500$  mV relatively to it with the potential sweep rate of  $10$  mV/s. Each experiment was performed in triplicate. The obtained polarisation curves were presented in the coordinates  $E(\lg i)$ , and the Tafel slopes ( $b$ ) and the corrosion current density ( $i_{corr}$ ) were evaluated from them [15]. Subsequently, the polarisation resistances ( $R_p$ ) were estimated from the Tafel slopes and the corrosion current densities using the Stern – Geary equation [16,17]:

$$R_p = \frac{1}{\ln 10} \cdot \frac{1}{i_{corr}} \cdot \frac{b_a \cdot |b_c|}{b_a + |b_c|}, \tag{5}$$

where  $b_a$  and  $b_c$  are the slopes of the anodic and cathodic branches of the polarisation curve. The inhibitory ability of the compound was estimated from the ratio of the corrosion current densities in the absence ( $i_0$ ) and in the presence ( $i$ ) of the inhibitor [11]:

$$IE = (i_0 - i) / i_0 \cdot 100\%, \tag{6}$$

and also from the ratio of the polarisation resistances in the presence ( $R$ ) and in the absence ( $R_0$ ) of the inhibitor using equation (4).

### 2.5. EIS studies

For EIS tests, electrodes were prepared similarly to that described in the previous section. An open circuit potential was recorded during 30 min. Impedance values were recorded at the open circuit potential value in the alternating current frequency interval from  $100$  mHz to  $10$  kHz with the potential amplitude of  $10$  mV. Each experiment was performed in triplicate. The obtained results were presented in the form of Bode and Nyquist plots [18].

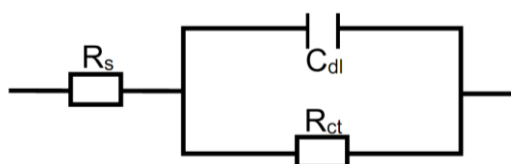


Figure 1. The Randles equivalent electrical circuit used to fit the EIS data

For the estimation of the impedance parameters, a simplified Randles equivalent electrical circuit (Figure 1) [19], containing the solution

resistance  $R_s$ , the consecutive charge transfer resistance  $R_{ct}$  of the passivation layer, and the parallel constant-phase element representing the double electric layer, was employed.

The impedance ( $Z$ ) of the Randles equivalent circuit is expressed by the equation [17]:

$$Z = R_s + \frac{1}{\frac{1}{R_{ct}} + P \cdot (i\omega)^n} = R_s + \frac{1}{\frac{1}{R_{ct}} + P \cdot \omega^n \cdot (\cos(\frac{n\pi}{2}) + i \sin(\frac{n\pi}{2}))}, \tag{7}$$

where  $\omega$  is the frequency of the alternating current,  $P$  and  $n$  are the parameters of the constant phase element.

The fitting of the equivalent circuit parameters to the experimental impedance values was performed using the free software EIS Spectrum Analyser [20]. In addition, the capacitance ( $C_{dl}$ ) and the thickness ( $d$ ) of the double electric layer were estimated [21]:

$$C_{dl} = P^{\frac{1}{n}} \cdot \left( \frac{R_s \cdot R_{ct}}{R_s + R_{ct}} \right)^{\frac{1-n}{n}}, \tag{8}$$

$$d = (S \cdot \epsilon_0 \cdot \epsilon) / C_{dl}. \tag{9}$$

where  $S$  is the electrode surface,  $\epsilon$  is the dielectric constant of water, and  $\epsilon_0 = 8.85 \cdot 10^{-12}$  F/m is the dielectric constant of vacuum.

The inhibitory ability of the compound was estimated from the ratio of the charge transfer resistances in the presence ( $R$ ) and in the absence ( $R_0$ ) of the inhibitor using equation (4) [11].

## 3. RESULTS AND DISCUSSION

### 3.1. Gravimetric studies

The dependence of the measured inhibition efficiencies at the different inhibitor concentrations ( $C_{inh}$ ) is presented in Table 1.

Table 1. Variation of corrosion rates and inhibition efficiencies for mild steel in 0.5 M HCl and 0.5 M H<sub>2</sub>SO<sub>4</sub> acid solutions with different concentrations of Fagus sylvatica purpurea fallen leaves extracts obtained in the gravimetric measurements

Medium	0.5 M HCl		0.5 M H <sub>2</sub> SO <sub>4</sub>	
	$\omega$ , mg/(cm <sup>2</sup> · h)	IE, %	$\omega$ , mg/(cm <sup>2</sup> · h)	IE, %
0	0.89 ± 0.08	–	1.1 ± 0.1	–
0.1	0.67 ± 0.07	24.9	0.81 ± 0.09	25.9
0.3	0.51 ± 0.06	43.1	0.72 ± 0.08	34.7
1	0.30 ± 0.04	66.3	0.54 ± 0.06	51.3
3	0.28 ± 0.04	67.9	0.40 ± 0.05	63.8
10	0.26 ± 0.04	70.8	0.26 ± 0.05	76.2

3.2. Polarisation studies

The graphs of the open circuit potential measurements are presented in Figure 2.

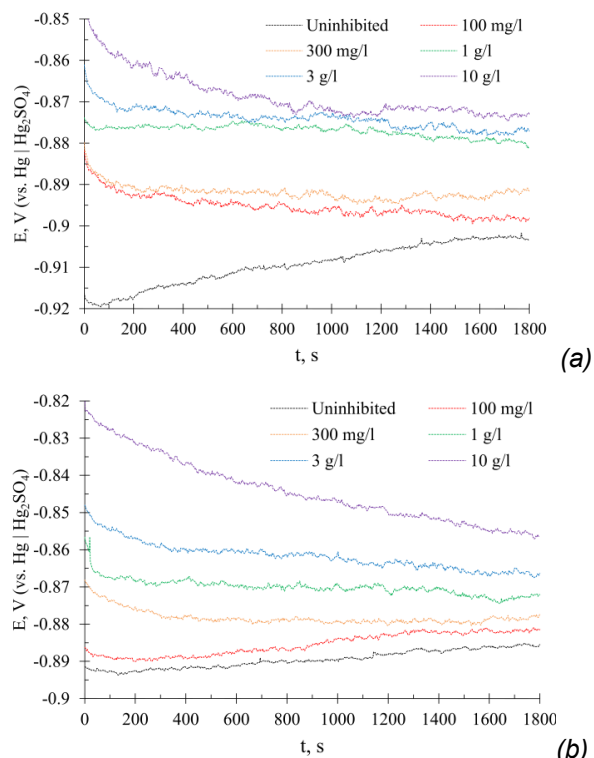


Figure 2. The open circuit potential of steel in (a) 0.5 M HCl, and (b) 0.5 M H<sub>2</sub>SO<sub>4</sub> with the different additions of the *Fagus sylvatica purpurea* leaf extract after 30 min of exposure

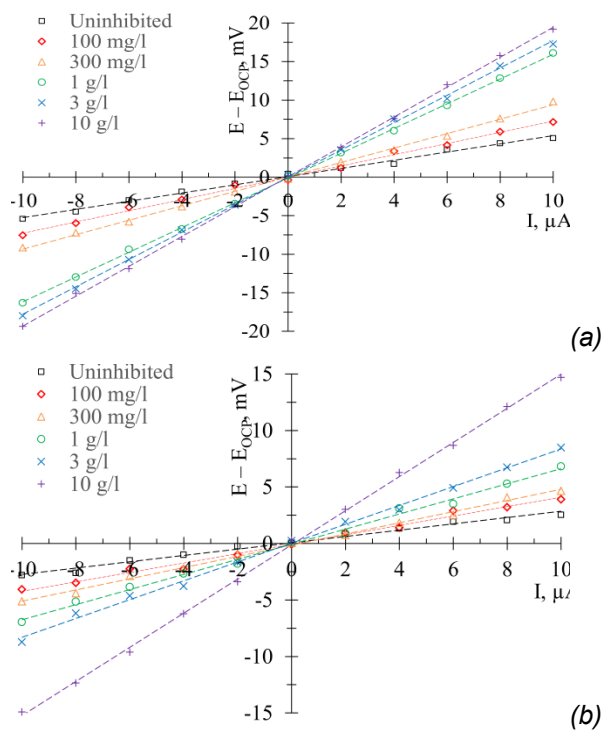


Figure 3. The linear polarisation resistance curves of steel in (a) 0.5 M HCl, and (b) 0.5 M H<sub>2</sub>SO<sub>4</sub> with the different additions of the *Fagus sylvatica purpurea* leaf extract

The results of the linear polarisation resistance measurements are presented in Figure 3 and in Table 2.

Table 2. Variation of the measured polarisation resistance and estimated inhibition efficiencies of mild steel in 0.5 M HCl and 0.5 M H<sub>2</sub>SO<sub>4</sub> acid solutions with different concentrations of *Fagus sylvatica purpurea* fallen leaves extracts

Medium	0.5 M HCl		0.5 M H <sub>2</sub> SO <sub>4</sub>		
	C <sub>inh</sub> , g/l	R <sub>p</sub> , Ohm · cm <sup>2</sup>	IE, %	R <sub>p</sub> , Ohm · cm <sup>2</sup>	IE, %
	0	520 ± 10	—	300 ± 10	—
	0.1	700 ± 20	25.2	450 ± 10	32.2
	0.3	950 ± 20	45.0	510 ± 20	40.0
	1	1460 ± 30	64.1	660 ± 20	53.3
	3	1640 ± 30	68.0	860 ± 20	64.4
	10	1790 ± 30	70.7	1540 ± 30	80.1

The results of the potentiodynamic polarisation measurements are presented in Figure 4 and in Table 3.

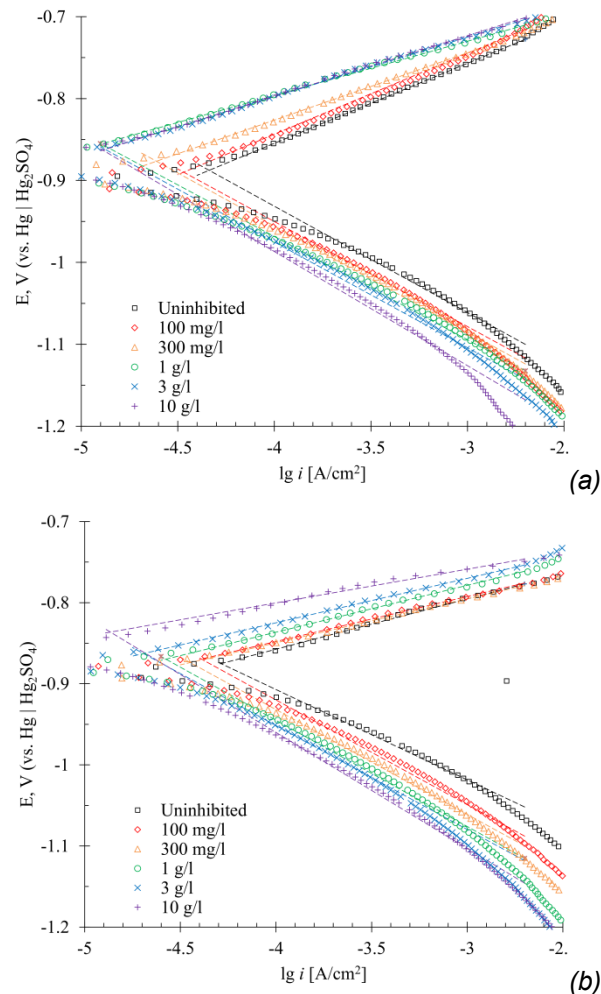



Figure 4. The polarisation curves of steel in (a) 0.5 M HCl, and (b) 0.5 M H<sub>2</sub>SO<sub>4</sub> with the different additions of the *Fagus sylvatica purpurea* leaf extract after 30 min of exposure

Table 3. Variation of the measured open circuit potentials, Tafel slopes of polarisation curves, and estimated corrosion current densities, polarisation resistance and inhibition efficiencies of mild steel in 0.5 M HCl and 0.5 M H<sub>2</sub>SO<sub>4</sub> acid solutions with different concentrations of *Fagus sylvatica purpurea* fallen leaves extracts

C <sub>inh</sub> , g/l	E <sub>cor</sub> , mV	b <sub>a</sub> , mV/dec	b <sub>c</sub> , mV/dec	i <sub>cor</sub> , μA/cm <sup>2</sup>	IE, %	R <sub>p</sub> , Ohm cm <sup>2</sup>	IE, %
0.5 M HCl with additions of <i>Fagus sylvatica purpurea</i> leaf extract							
0	-903	98.8	-129.8	45.9	-	527	-
0.1	-898	92.7	-128.3	33.9	26.1	715	26.3
0.3	-892	82.2	-129.6	24.5	46.7	891	40.9
1	-881	66.1	-126.1	12.7	71.2	1482	64.5
3	-877	74.0	-129.1	12.9	71.8	1529	65.5
10	-873	72.7	-129.4	13.2	72.4	1622	67.6
0.5 M H <sub>2</sub> SO <sub>4</sub> with additions of <i>Fagus sylvatica purpurea</i> leaf extract							
0	-886	65.2	-131.4	51.7	-	335	-
0.1	-881	55.5	-129.2	40.8	21.2	414	19.1
0.3	-877	52.3	-129.3	35.6	31.1	466	28.2
1	-872	47.8	-130.0	26.6	48.5	655	48.9
3	-865	44.2	-128.2	20.3	60.7	821	59.2
10	-857	41.6	-133.0	13.6	73.6	1026	67.4

### 3.3. EIS studies

The results of electrochemical impedance measurements are presented in Figure 5 and in Table 4.

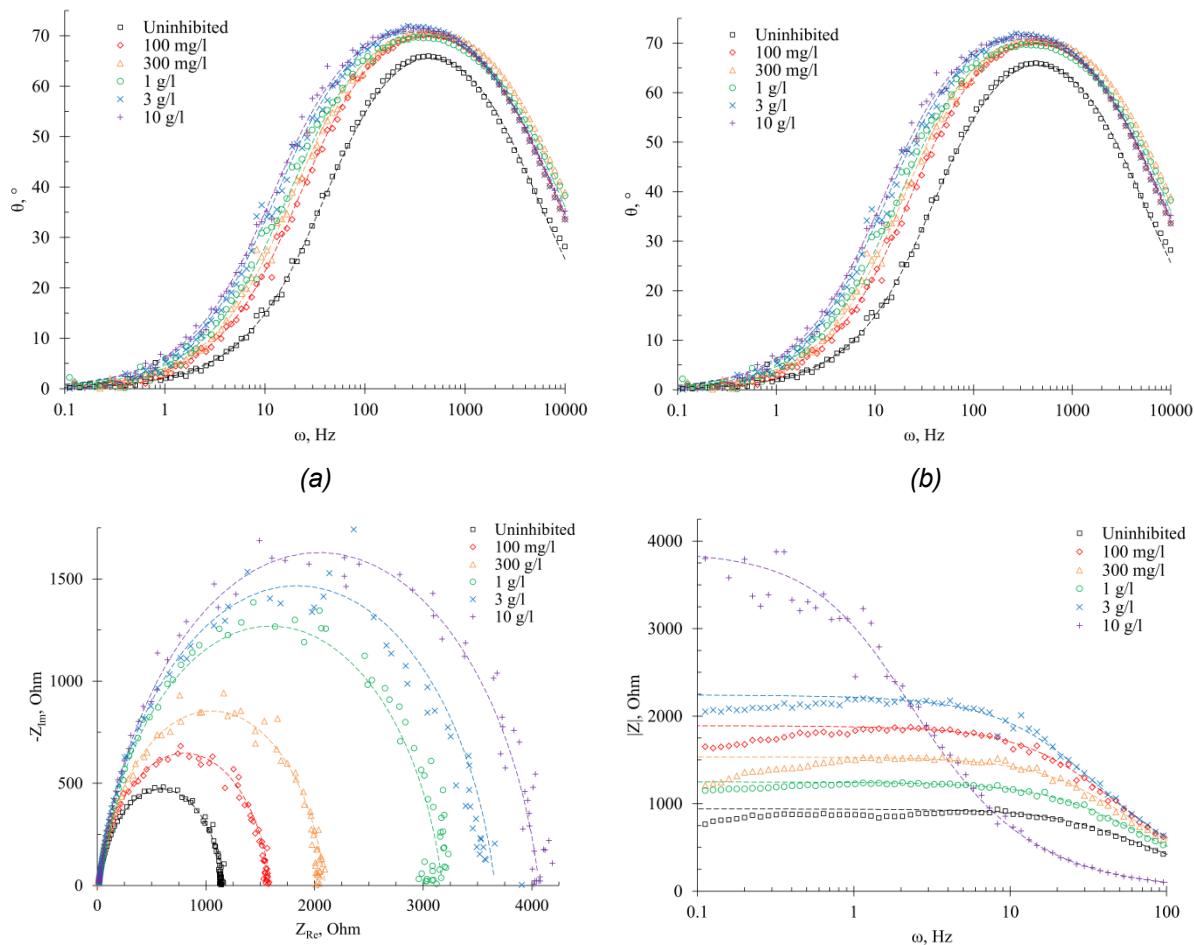



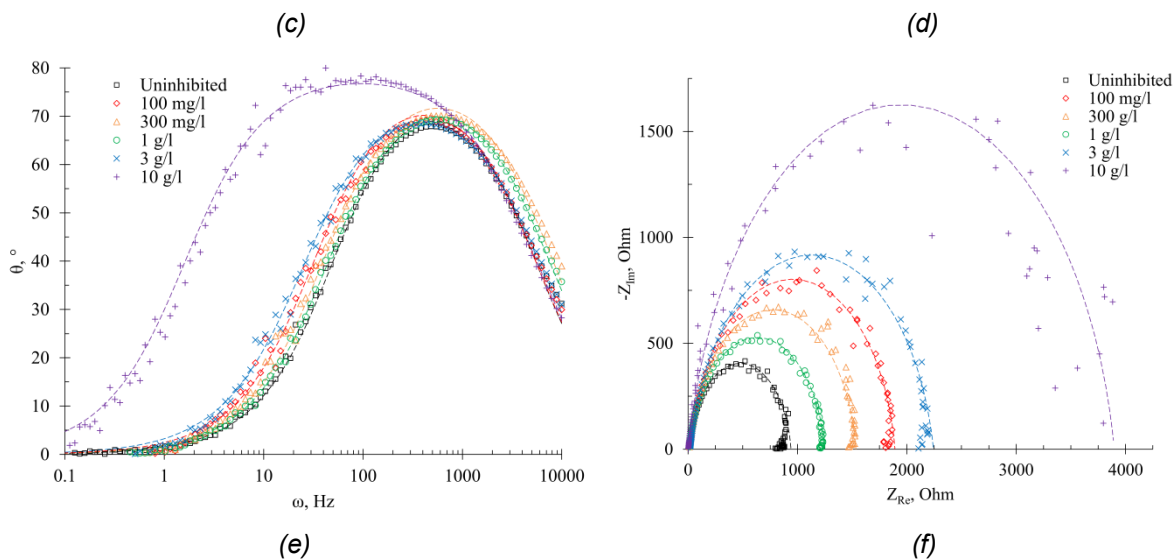


Figure 5. The Bode plots of steel in (a), (b) 0.5 M HCl, and (d), (e) 0.5 M H<sub>2</sub>SO<sub>4</sub>, and the Nyquist plots of steel in (c) 0.5 M HCl, and (f) 0.5 M H<sub>2</sub>SO<sub>4</sub> with the different additions of the *Fagus sylvatica purpurea* leaf extract after 30 min of exposure

Table 4. Variation of the estimated electrochemical parameters obtained in the electrochemical impedance measurements and of inhibition efficiencies of mild steel in 0.5 M HCl and 0.5 M H<sub>2</sub>SO<sub>4</sub> acid solutions with different concentrations of *Fagus sylvatica purpurea* fallen leaves extracts

<i>c<sub>inh</sub></i> , g/l	<i>R<sub>s</sub></i> , Ohm	<i>P</i> , μOhm <sup>-1</sup> · s <sup><i>n</i></sup>	<i>n</i>	<i>C<sub>dl</sub></i> , μF	<i>d</i> , nm	<i>R<sub>ct</sub></i> , Ohm	IE, %
0.5 M HCl with additions of <i>Fagus sylvatica purpurea</i> leaf extract							
0	17.0	67.6	0.88	26.8	1.04	1144.7	–
0.1	9.9	82.4	0.87	28.4	0.98	1583.5	27.7
0.3	9.8	71.3	0.87	24.1	1.15	2087.0	45.1
1	14.8	55.7	0.86	17.5	1.58	3163.2	63.8
3	14.4	60.7	0.86	19.3	1.44	3645.5	68.6
10	14.7	59.1	0.86	18.8	1.48	4052.8	71.7
0.5 M H <sub>2</sub> SO <sub>4</sub> with additions of <i>Fagus sylvatica purpurea</i> leaf extract							
0	13.3	55.6	0.91	342	0.08	927.4	–
0.1	12.5	50.9	0.90	290	0.10	1237.1	25.0
0.3	12.5	43.0	0.91	256	0.11	1521.8	39.1
1	18.5	44.5	0.90	261	0.11	1873.1	50.4
3	18.1	52.7	0.88	279	0.10	2225.4	59.3
10	2.8	32.9	0.89	138	0.20	3894.1	76.2

### 3.4. Langmuir adsorption model

The description of the adsorption of the leaf extract components on the steel surface was performed in terms of the Langmuir adsorption model, because this model is simple and used in most corrosion inhibition studies [22]. The Langmuir adsorption isotherm equation was linearised in the form:

$$c_{inh} / \theta = 1 / K_{ads} + c_{inh}, \tag{10}$$

where *c<sub>inh</sub>* is the concentration of the *Fagus sylvatica purpurea* leaf extract solution, *K<sub>ads</sub>* is the adsorption-desorption equilibrium constant, and  $\theta$  is the degree of surface coverage which represents

the fraction of the surface of the metal covered by the inhibitor molecules adsorbed on to the metal surface. It is connected to the inhibition efficiency, IE of the inhibitor through the relation:

$$IE = \theta \cdot 100\% \tag{11}$$

The dependencies of *c<sub>inh</sub>*/θ on *c<sub>inh</sub>* are presented in Figure 6 and in Table 5.

The data were processed using the least squares technique [23], and the equilibrium constants *K<sub>ads</sub>* were estimated as the intercepts of the regression equations. The Gibbs energy changes of the sorption ( $\Delta_{ads}G$ ) were estimated from the equation:

$$\Delta_{ads}G = -RT \ln (K_{ads} \cdot c_{water}), \quad (12) \quad \text{where } c_{water} = 10^3 \text{ g/l is the water concentration in the extracts. The results are presented in Table 5.}$$

Table 5. The estimated parameters of the Langmuir adsorption model, sorption-desorption equilibrium constants and the Gibbs energies of adsorption for the sorption of *Fagus sylvatica purpurea* fallen leaves extracts on the steel surface

$C_{inh}$ , g/l	$\theta$	$C_{inh} / \theta$ , g/l	Regression equation	$K_{ads}$ , l/g	$\Delta_{ads}G$ , kJ/mol
0.5 M HCl with additions of <i>Fagus sylvatica purpurea</i> leaf extract					
0.1	0.261	0.383	$C_{inh} / \theta = (1.36 \pm 0.01) \cdot C_{inh} + (0.16 \pm 0.06);$ $R^2 = 0.999$	$7 \pm 3$	$-21 \pm 2$
0.3	0.467	0.642			
1	0.712	1.404			
3	0.718	4.178			
10	0.724	13.812			
0.5 M H <sub>2</sub> SO <sub>4</sub> with additions of <i>Fagus sylvatica purpurea</i> leaf extract					
0.1	0.212	0.472	$C_{inh} / \theta = (1.31 \pm 0.04) \cdot C_{inh} + (0.6 \pm 0.2);$ $R^2 = 0.997$	$1.8 \pm 0.6$	$-18 \pm 2$
0.3	0.311	0.965			
1	0.485	2.062			
3	0.607	4.942			
10	0.736	13.587			

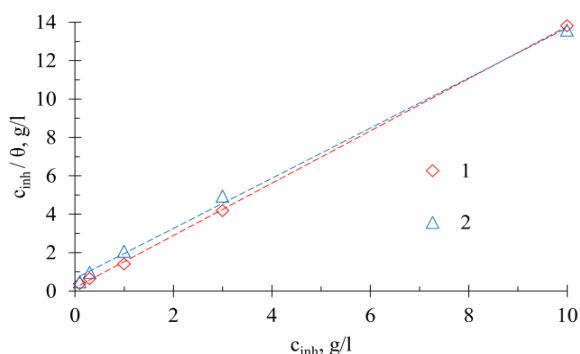


Figure 6. The plots of  $c_{inh} / \theta$  vs.  $c_{inh}$  for the adsorption of the *Fagus sylvatica purpurea* leaf extract on the steel surface

### 3.5. Discussion

The results of the open circuit potential measurements show that with the addition of a

*Fagus sylvatica purpurea* leaf extract the potential of the mild steel both in the solution of 0.5 M HCl and 0.5 M H<sub>2</sub>SO<sub>4</sub> shifts to the more positive values. In addition, the Tafel slopes of the anodic branches of the polarisation curves decrease with alteration of the extract concentration, whereas the slopes of the cathodic branches remain nearly the same. This implies that in the solutions of both acids the purple beech leaf extract acts as the anodic-type inhibitor [24,25].

The values of the inhibition efficiencies estimated from the data of gravimetric, electrochemical and EIS experiments coincide well and show the similar trend (see Table 6). The values of the polarisation resistance of the absorbed inhibitor estimated from the data of linear polarisation and from the Tafel slopes also coincide well.

Table 6. The comparison of the inhibition efficiencies of *Fagus sylvatica purpurea* fallen leaves extracts obtained by the various methods

$C_{inh}$ , g/l	Inhibition efficiency, %				
	Gravimetric experiment	Linear polarisation resistance	Corrosion current density	Calculated polarisation resistance	Charge transfer resistance
0.5 M HCl with additions of <i>Fagus sylvatica purpurea</i> leaf extract					
0.1	24.9	25.2	26.1	26.3	27.7
0.3	43.1	45.0	46.7	40.9	45.1
1	66.3	64.1	71.2	64.5	63.8
3	67.9	68.0	71.8	65.5	68.6
10	70.8	70.7	72.4	67.6	71.7
0.5 M H <sub>2</sub> SO <sub>4</sub> with additions of <i>Fagus sylvatica purpurea</i> leaf extract					
0.1	25.9	32.2	21.2	19.1	25.0
0.3	34.7	40.0	31.1	28.2	39.1
1	51.3	53.3	48.5	48.9	50.4
3	63.8	64.4	60.7	59.2	59.3

10	76.2	80.1	73.6	67.4	76.2
----	------	------	------	------	------

With the increase of the extract concentration from 0.1 to 1 g/l its inhibition efficiency on the corrosion of mild steel EN Fe37-3FN in a 0.5 M hydrochloric acid medium rises from ~25–30% to ~65–70%, but the further concentration increase gives no significant improvement of the inhibition efficiency. In contrast, the inhibition efficiency of the extract on the corrosion of the same steel in a 0.5 M sulphuric acid medium continues to increase with the rise of extract concentration, and approaches ~70–75% when the concentration of 10 g/l is achieved.

The adsorption of the extracted components on the steel surface fairly obeys the Langmuir adsorption model. The values of the sorption–desorption equilibrium constants and the Gibbs energies of sorption estimated using the degrees of surface coverage obtained from the different methods coincide within their ranges of uncertainty. The calculated Gibbs energies of sorption are in the range ~ –20 kJ/mol for both hydrochloric and sulphuric acids, which means that the nature of the adsorption is physical due to the electrostatic interactions [26].

Despite the experimental values of the inhibition efficiencies may vary significantly with alteration of both the solution composition and temperature [27], the leaf extracts of *Fagus sylvatica purpurea* revealed the prospective inhibition potential against the corrosion of mild steel in acidic environments. The addition of common beech leaf extracts to a corrosive environment can be used to protect equipment from corrosion in pickling areas of metal processing industries, and in electroplating baths. The extracts may also be used as the part of products for removing corrosion products from steel surfaces [28,29]. Moreover, using the freshly fallen leaves for extract preparation does not put the trees into danger, and could contribute to the biomass waste usage.

#### 4. CONCLUSION

The inhibitory ability of the *Fagus sylvatica purpurea* leaf boiling extracts on the corrosion of mild steel EN Fe37-3FN in 0.5 M hydrochloric acid and 0.5 M sulphuric acid media was investigated using the gravimetric, electrochemical, and EIS methods. It was shown that the addition of 100 mg/l of the extract reduces the corrosion rate in HCl by 25% and in H<sub>2</sub>SO<sub>4</sub> by 20–25%, and that of 1 g/l – by 65–70% and 45–50%, respectively, whereas the addition of 10 g/l of the extract further reduces the corrosion rate in H<sub>2</sub>SO<sub>4</sub> by 70–75%. The inhibition efficiency values obtained by the various methods show the similar trends. The adsorption of the extract components on a steel surface follows the Langmuir adsorption model, and the nature of

adsorption is physical. The *Fagus sylvatica purpurea* leaf extract shows itself as prospective and environmentally friendly substance for reducing the steel corrosion rate in acidic environments.

#### 5. REFERENCES

- [1] R.Haldhar, S.C.Kim, E.Berdimurodov, D.K.Verma, C.M.Hussain (2021) Corrosion inhibitors: industrial applications and commercialization, book Sustainable corrosion inhibitors II: Synthesis, design, and practical applications, ACS Symposium Series, Vol. 1404, American Chemical Society, p. 219-235. <https://doi.org/10.1021/bk-2021-1404.ch010>.
- [2] N.Vaszilcsin, A.Kellenberger, M.L.Dan, D.A.Duca, V.L.Ordodi (2023) Efficiency of Expired Drugs Used as Corrosion Inhibitors: A Review, Materials, 16(16), 5555. <https://doi.org/10.3390/ma16165555>.
- [3] A.Thakur, S.Sharma, R.Ganjoo, H.Assad, A.Kumar (2022) Anti-corrosive potential of the sustainable corrosion inhibitors based on biomass waste: a review on preceding and perspective research, book Journal of Physics: Conference Series, Vol. 2267, No. 1, IOP Publishing, p. 012079. <https://doi.org/10.1088/1742-6596/2267/1/012079>.
- [4] S.Marzorati, L.Verotta, S.P.Trasatti (2018) Green corrosion inhibitors from natural sources and biomass wastes, Molecules, 24(1), 48. <https://doi.org/10.3390/molecules24010048>.
- [5] M.Ž.Nonić, D.M.Skočajić, M.N.Grbic, M.T.Šijačić-Nikolić (2017) Variability of Quantitative and Qualitative Characteristics of *Fagus sylvatica 'Purpurea'* Clones Produced by Grafting, Notulae Botanicae Horti Agrobotanici Cluj-Napoca, 45(2), 400-407. <https://doi.org/10.15835/nbha45210896>.
- [6] T.Hofmann, E.Nebhaj, É.Stefanovits-Bányai, L.Albert (2015) Antioxidant capacity and total phenol content of beech (*Fagus sylvatica L.*) bark extracts, Industrial Crops and Products, 77, 375-381. <https://doi.org/10.1016/j.indcrop.2015.09.008>.
- [7] L.Pirvu, A.Grigore, C.Bubueanu, E.Draghici (2013) Comparative analytical and antioxidant activity studies on a series of *Fagus sylvatica L.* leaves extracts, JPC-Journal of Planar Chromatography-Modern TLC, 26(3), 237-242. <https://doi.org/10.1556/jpc.26.2013.3.6>.
- [8] M.Formato, F.Scharenberg, S.Pacifico, C.Zidorn (2022) Seasonal variations in phenolic natural products in *Fagus sylvatica* (European beech) leaves, Phytochemistry, 203, 113385. <https://doi.org/10.1016/j.phytochem.2022.113385>.
- [9] E.Cadahía, B.Fernández de Simón, I.Aranda, M.Sanz, D.Sánchez-Gómez, E.Pinto (2015) Non-targeted metabolomic profile of *Fagus sylvatica L.* leaves using liquid chromatography with mass spectrometry and gas chromatography with mass spectrometry. Phytochemical Analysis, 26(2), 171-182. <https://doi.org/10.1002/pca.2549>.
- [10] N.Bhardwaj, P.Sharma V.Kumar (2021) Phytochemicals as steel corrosion inhibitor: an insight into mechanism, Corrosion Reviews, 39(1), 27-41. <https://doi.org/10.1515/corrrev-2020-0046>.



- [11] A.Kadhim A.A.Al-Amiery R.Alazawi M.K.S.Al-Ghezi R.H.Abass (2021) Corrosion inhibitors. A review, *International Journal of Corrosion and Scale Inhibition*, 10(1), 54-67. <https://doi.org/10.17675/2305-6894-2021-10-1-3>.
- [12] V.I.Vorobyova, M.I.Skiba, A.S.Shakun, S.V.Nahirniak (2019) Relationship between the inhibition and antioxidant properties of the plant and biomass wastes extracts-A Review, *International Journal of Corrosion and Scale Inhibition*, 8(2), 150-178. <https://doi.org/10.17675/2305-6894-2019-8-2-1>.
- [13] A.Cojocar, I.Maior, D.I.Vaireanu, C.Lingvay, I.Lingvay, S.Caprarescu, G.E.Badea (2010) Ethanol extract of *Fagus Sylvatica* leaves as an eco-friendly inhibitor for carbon steel corrosion in acidic solutions, *Journal of Sustainable Energy*, 1(3), 64-71.
- [14] J.Tafel (1905) Über die Polarisation bei kathodischer Wasserstoffentwicklung, *Zeitschrift für Physikalische Chemie*, 50(1), 641-712. <https://doi.org/10.1515/zpch-1905-5043>.
- [15] F.Mansfeld (1973) Tafel slopes and corrosion rates from polarization resistance measurements, *Corrosion*, 29(10), 397-402. <https://doi.org/10.5006/0010-9312-29.10.397>.
- [16] M.Stern (1958) A method for determining corrosion rates from linear polarization data, *Corrosion*, 14(9), 60-64. <https://doi.org/10.5006/0010-9312-14.9.60>.
- [17] M.Stern, A.L.Geary (1957) Electrochemical polarization: I. A theoretical analysis of the shape of polarization curves, *Journal of Electrochemical Society*, 104(1), 56-63. <https://doi.org/10.1149/1.2428496>.
- [18] X.Z.Yuan, C.Song, H.Wang, J.Zhang (2010) EIS equivalent circuits, book *Electrochemical Impedance Spectroscopy in PEM Fuel Cells: Fundamentals and Applications*, Berlin, Springer, p. 139-192. [https://doi.org/10.1007/978-1-84882-846-9\\_4](https://doi.org/10.1007/978-1-84882-846-9_4).
- [19] J.E.B.Randles (1947) Kinetics of rapid electrode reactions, *Discussions of the Faraday Society*, 1, 11-19. <https://doi.org/10.1039/DF9470100011>.
- [20] A.S.Bondarenko G.A.Ragoisha (2005) Inverse problem in potentiodynamic electrochemical impedance spectroscopy, book *A.L.Pomerantsev. Progress in Chemometrics Research*, New York, Nova Science Publishers, p. 89-102, <https://www.abc.chemistry.bsu.by/vi/analyser>.
- [21] A.Lasia (2014) *Electrochemical Impedance Spectroscopy and its Applications*, Springer, New York. <https://doi.org/10.1007/978-1-4614-8933-7>.
- [22] I.Langmuir (1918) The adsorption of gases on plane surfaces of glass, mica and platinum, *Journal of the American Chemical Society*, 40(9), 1361-1403. <https://doi.org/10.1021/ja02242a004>.
- [23] R.Adrain (1808) Research concerning the probabilities of the errors which happen in making observations, &c, *The Analyst; Or Mathematical Museum*, 1(4), 93-109.
- [24] S.-I.Pyun (2021) Strategies of metal corrosion protection, *ChemTexts*, 7(1), 2. <https://doi.org/10.1007/s40828-020-00121-y>.
- [25] X.Xie, R.Holze (2018) Experimental methods in corrosion research, *ChemTexts*, 4(1), 5-13. <https://doi.org/10.1007/s40828-018-0057-0>.
- [26] A.Kokalj (2022) Corrosion inhibitors: physisorbed or chemisorbed? *Corrosion Science*, 196, 109939. <https://doi.org/10.1016/j.corsci.2021.109939>.
- [27] A.B.Kičenko, V.M.Kušnarenko (2005) O nekorrektnosti točnyh značenij ocenki zašitnogo dejstviâ inhibitorov korrozii, *Praktika protivokorozionnoj zašity*, 4(38), 17-22.
- [28] T.J.Harvey, F.C.Walsh, A.H.Nahlé (2018) A review of inhibitors for the corrosion of transition metals in aqueous acids, *Journal of Molecular Liquids*, 266, 160-175. <https://doi.org/10.1016/j.molliq.2018.06.014>.
- [29] M.Goyal et al (2018) Organic corrosion inhibitors for industrial cleaning of ferrous and non-ferrous metals in acidic solutions: A review, *J. of Molecular Liquids*, 256, 565-573. <https://doi.org/10.1016/j.molliq.2018.02.045>.

## IZVOD

### INHIBITORNA SVOJSTVA EKSTRAKATA IZ OPALOG LIŠĆA *FAGUS SILVATICA PURPUREA* NA KOROZIJU BLAGOG ČELIKA U KISELIM SREDINAMA

*Inhibiciona sposobnost ekstrakata iz opalog lišća Fagus silvatica purpurea na koroziju mekog čelika EN Fe37-3FN u 0,5 M medijumu hlorovodonične kiseline i 0,5 M sumporne kiseline ispitivana je gravimetrijskim, elektrohemijskim i EIS metodama. Pokazalo se da dodatak 100 mg/l ekstrakta opalog lišća Fagus silvatica purpurea smanjuje stopu korozije za 20–25%, a od 1 g/l i više – za 65–70%. Adsorpcija komponenti ekstrakta na čeličnoj površini prati Langmuir model adsorpcije, a priroda adsorpcije je fizička. Ekstrakt opalog lišća Fagus silvatica purpurea pokazuje se kao perspektivna i ekološki prihvatljiva supstanca za smanjenje stope korozije čelika u kiselim sredinama.*

**Ključne reči:** *Fagus silvatica purpurea, ljubičasta bukva, ključajući ekstrakti, inhibicija korozije u kiseloj sredini, blagi čelik, gravimetrijska studija, elektrohemijska studija, spektroskopija elektrohemijske impedanse, Langmuir adsorpciona izoterma*

Naučni rad

Rad primljen: 29.02.2024.

Rad korigovan: 24.09.2024.

Rad prihvaćen: 01.10.2024.

Pavel Anatolyevich Nikolaychuk: <https://orcid.org/0000-0003-0335-3955>

© 2024 Authors. Published by Engineering Society for Corrosion. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution 4.0 International license (<https://creativecommons.org/licenses/by/4.0/>)